



Libraries and Learning Services

University of Auckland Research Repository, ResearchSpace

Version

This is the publisher's version. This version is defined in the NISO recommended practice RP-8-2008 <http://www.niso.org/publications/rp/>

Suggested Reference

Legg, M., & Bradley, S. (2016). Measurement of stiffness of standing trees and felled logs using acoustics: A review. *The Journal of the Acoustical Society of America*, 139(2), 588-604. doi: [10.1121/1.4940210](https://doi.org/10.1121/1.4940210)

Copyright

Items in ResearchSpace are protected by copyright, with all rights reserved, unless otherwise indicated. Previously published items are made available in accordance with the copyright policy of the publisher.

http://acousticalsociety.org/for_authors/posting_guidelines

<http://www.sherpa.ac.uk/romeo/issn/0001-4966/>

<https://researchspace.auckland.ac.nz/docs/uoa-docs/rights.htm>

Measurement of stiffness of standing trees and felled logs using acoustics: A review

Mathew Legg^{a)} and Stuart Bradley

Department of Physics, University of Auckland, Auckland, New Zealand

(Received 22 May 2015; revised 20 December 2015; accepted 7 January 2016; published online 2 February 2016)

This paper provides a review on the use of acoustics to measure stiffness of standing trees, stems, and logs. An outline is given of the properties of wood and how these are related to stiffness and acoustic velocity throughout the tree. Factors are described that influence the speed of sound in wood, including the different types of acoustic waves which propagate in tree stems and lumber. Acoustic tools and techniques that have been used to measure the stiffness of wood are reviewed. The reasons for a systematic difference between direct and acoustic measurements of stiffness for standing trees, and methods for correction, are discussed. Other techniques, which have been used in addition to acoustics to try to improve stiffness measurements, are also briefly described. Also reviewed are studies which have used acoustic tools to investigate factors that influence the stiffness of trees. These factors include different silvicultural practices, geographic and environmental conditions, and genetics. © 2016 Acoustical Society of America.

[<http://dx.doi.org/10.1121/1.4940210>]

[JFL]

Pages: 588–604

I. INTRODUCTION

There can be significant variation in the properties of wood, even within trees in the same stand.^{1,2} Examples of wood properties of interest include stiffness, density, microfibril angle, fiber length, spiral grain, reaction wood (compressional or tension wood), shrinkage, checking, and resin pockets. The importance of measuring wood properties is discussed in Refs. 3–10. A significant amount of effort has, therefore, been put into developing non-destructive testing (NDT) techniques for measuring these properties.

One of the main wood properties of interest to the wood industry is stiffness, which is related to the Modulus of Elasticity (MOE) or Young's modulus. Structural grade timber should have high stiffness levels. By performing segregation at the standing tree or log stage, considerable saving can be achieved in terms of reduction in wastage of wood and reduced manufacturing costs. Also, measurements of stiffness can be used to improve breeding, planting, and silviculture practices so that future forests have higher stiffness characteristics.

Bending tests can be used to measure the static modulus of elasticity of samples cut from logs. Saw milling production line bending tools have been developed for lumber. However, performing segregation at this stage in the production process can potentially cause significant wastage in wood and manufacturing costs. It is, therefore, desirable to measure the stiffness at the log or standing tree stage using NDT methods.⁶ Techniques have been developed for standing trees, which either physically bend a tree stem¹¹ or measure the natural frequency of tree stem sway.¹² However, these techniques do not appear to be commonly used.

The stiffness of wood can also be estimated by measuring other wood properties. The SilviScan¹³ estimates stiffness by

measuring the average microfibril angle using x-ray diffraction for cylindrical cores taken from trees.¹⁴ However, it has been reported that this technique has the disadvantage of being more costly than alternative techniques such as acoustics and requires samples to be sent away for testing.¹⁵ Near infrared (NIR) spectroscopy has also been used for profiling the stiffness distribution in sawmilling application.¹⁶ X-ray tomography has shown the ability to provide good imaging of the density and internal structure, such as knots, of logs but also has the disadvantage of being relatively expensive and not suited to field based measurements.¹⁷

Acoustic techniques have been developed for measuring the stiffness of wood. They are among the most commonly used techniques because they are relatively inexpensive, fast, robust, and easily used in the field. Acoustic techniques are used for segregation of existing forests by measuring the stiffness of standing trees, felled logs, or sawn timber. They are also used for improving the stiffness of future forests in breeding studies. Commercial acoustic tools have been developed for either measuring the stiffness of logs or standing trees. These tools can be hand held devices, installations in saw milling or timber processing plants, or more recently harvester head attachments.

There are books and review papers on the acoustics of wood.^{18–26} Bucur's book provides an extensive review on this topic.²⁴ Similarly there are books and review papers on NDT of wood, that includes the use of acoustics.^{27–37} While they do mention the use of acoustics for stiffness measurements of tree stems, they do not focus in any great detail on this topic and may be in need of updating. Literature reviews have been written relating to the stiffness of wood,^{34,38,39} but these have not specifically focused on the use of acoustics. Walker and Nakada provided a review on stiffness and acoustics.⁴⁰ However, this was written some time ago and there has been significant work performed on this topic since then. Wang *et al.*⁴¹ reviewed studies relating to differences

^{a)}Electronic mail: m.legg@auckland.ac.nz

in measured stiffness that were obtained for acoustic velocity measurements made on standing trees and logs. No paper/book was found that provided a full/extensive review specifically on the use of acoustics for measuring the stiffness of wood. This paper was written in response to this gap in the literature.

This paper provides a review on literature relating to the use of acoustics for measuring the stiffness of wood in standing trees and felled logs. An overview of the properties of wood that affect acoustic velocity and how this relates to stiffness/MOE are discussed in Sec. II. Different types of acoustic waves, which propagate in tree stems and lumber, and their relative sound speed characteristics are also described. In Sec. III, methods, hardware, and errors for measuring the acoustic velocity in trees and logs are described. The systematic overestimation for measurements made in trees compared to logs and corrections are described in Sec. IV. Theories that have been proposed to explain this overestimation are discussed. Other techniques that have been used with acoustics for improving stiffness measurements are briefly outlined in Sec. V. In Sec. VI, literature is reviewed that have used acoustic tools to study factors influencing the stiffness of trees, such as silvicultural practices, geographic and environmental conditions, and genetics.

II. FACTORS INFLUENCING ACOUSTIC VELOCITY IN WOOD

The speed of sound in wood is related to a number of factors including mechanical properties, moisture content, temperature, and variations in grain angle. The acoustic wave speed also depends the type of waves that are propagating; dilatational (bulk) waves or “rod waves” (guided waves). This section provides an overview of the factors which affects acoustic velocity in wood.

A. Mechanical properties of wood

1. Hooke's law

Hooke's law describes the strain γ that occurs when a stress σ is applied to a sample. This is can be expressed as

$$\gamma_{ij} = S_{ijkl}\sigma_{kl}, \quad (1)$$

where S is the compliance tensor and the subscripts i, j, k , and l have values of 1, 2, or 3. The convention for σ_{kl} is that index k defines which face the stress is applied to (face 1 is in the 2–3 plane for an orthogonal system) and l is for the direction of the stress force (see Fig. 1). If symmetry is assumed, then $\sigma_{kl} = \sigma_{lk}$ and there are only six distinct stress components; $\sigma_{11}, \sigma_{22}, \sigma_{33}, \sigma_{23}, \sigma_{13}$, and σ_{12} . If these are written as a 6×1 vector $\hat{\sigma}$, then Eq. (1) becomes

$$\hat{\gamma} = \hat{S}\hat{\sigma}, \quad (2)$$

where $\hat{\gamma}$ is a 6×1 vector and \hat{S} is a 6×6 matrix (refer to Ref. 42).

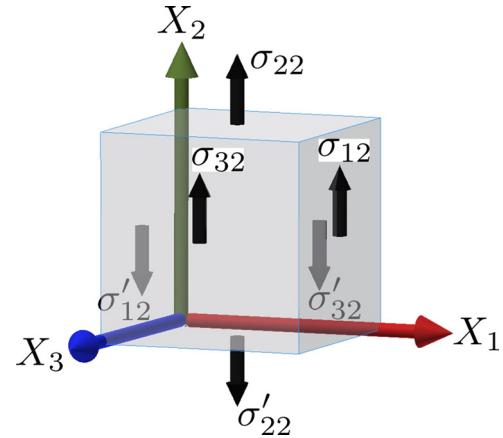


FIG. 1. (Color online) Diagram reproduced from Ref. 42 showing compressional and shear stresses in the X_2 axis direction for a small cubic sample at equilibrium.

2. Orthotropic mechanical properties of wood

Wood is an orthotropic medium, which means its properties vary in three orthogonal directions. For trees, it is convenient to use a cylindrical coordinate system, with orthotropic axes directions being in the longitudinal, radial, and tangential directions, respectively (see Fig. 2). Instead of using axes indexes 1, 2, and 3 it is common to instead use the corresponding indexes L , R , and T . This convention will be used in this work.

The compliance tensor for wood may be written as a 6×6 matrix

$$\hat{S} = \begin{bmatrix} \frac{1}{E_L} & -\frac{\nu_{RL}}{E_R} & -\frac{\nu_{TL}}{E_T} & 0 & 0 & 0 \\ -\frac{\nu_{LR}}{E_L} & \frac{1}{E_R} & -\frac{\nu_{TR}}{E_T} & 0 & 0 & 0 \\ -\frac{\nu_{LT}}{E_L} & -\frac{\nu_{RL}}{E_R} & \frac{1}{E_T} & 0 & 0 & 0 \\ 0 & 0 & 0 & \frac{1}{G_{RT}} & 0 & 0 \\ 0 & 0 & 0 & 0 & \frac{1}{G_{LT}} & 0 \\ 0 & 0 & 0 & 0 & 0 & \frac{1}{G_{LR}} \end{bmatrix}, \quad (3)$$

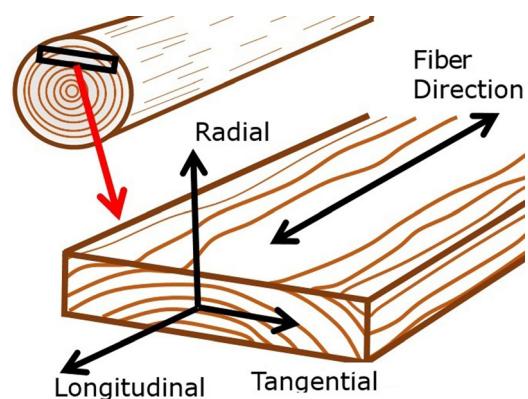


FIG. 2. (Color online) Diagram showing the orthotropic axes for wood.

TABLE I. Example Poisson's ratios for wood.

	ν_{LR}	ν_{LT}	ν_{RT}	ν_{TR}	ν_{RL}	ν_{TL}
Softwood average (Ref. 42)	0.37	0.42	0.47	0.35	0.041	0.033
Sitka spruce (Ref. 276)	0.372	0.467	0.435	0.245	0.040	0.025
Douglas fir (Ref. 276)	0.292	0.449	0.390	0.374	0.036	0.029

where E_L , E_R , and E_T are the Young's moduli in the longitudinal, radial, and tangential directions, ν_{RL} , ν_{LR} , ν_{TL} , ν_{LT} , ν_{TR} , and ν_{RT} are the Poisson's ratios, and G_{RT} , G_{LT} , and G_{LR} are the shear moduli. Table I provides some example Poisson's ratios for wood found in the literature. Bodig and Jayne⁴² states that ν_{RL} and ν_{TL} are typically much lower than the other Poisson's ratios and are, therefore, subject to large measurement errors.

It should be noted that the above compliance tensor is different from that for an isotropic medium, such as steel, which has a single Young's modulus E , shear modulus $G = E/[2(1 + \nu)]$, and Poisson's ratio ν . For the isotropic case, \hat{S} becomes⁴²

$$\hat{S} = \frac{1}{E} \begin{bmatrix} 1 & -\nu & -\nu & 0 & 0 & 0 \\ -\nu & 1 & -\nu & 0 & 0 & 0 \\ -\nu & -\nu & 1 & 0 & 0 & 0 \\ 0 & 0 & 0 & 2(1+\nu) & 0 & 0 \\ 0 & 0 & 0 & 0 & 2(1+\nu) & 0 \\ 0 & 0 & 0 & 0 & 0 & 2(1+\nu) \end{bmatrix}. \quad (4)$$

The compliance matrix is also commonly expressed in terms of its inverse $\hat{C} = \hat{S}^{-1}$, which is referred to as the stiffness matrix. For an orthotropic medium, this has the form

$$\hat{C} = \begin{bmatrix} C_{11} & C_{12} & C_{13} & 0 & 0 & 0 \\ C_{21} & C_{22} & C_{23} & 0 & 0 & 0 \\ C_{31} & C_{32} & C_{33} & 0 & 0 & 0 \\ 0 & 0 & 0 & C_{44} & 0 & 0 \\ 0 & 0 & 0 & 0 & C_{55} & 0 \\ 0 & 0 & 0 & 0 & 0 & C_{66} \end{bmatrix}. \quad (5)$$

Both the compliance and stiffness matrices are usually assumed to be symmetric, $\hat{S}_{kl} = \hat{S}_{lk}$ and $\hat{C}_{kl} = \hat{C}_{lk}$.

The key parameter that is used for determining if wood is of structural grade is the stiffness, which is related to the longitudinal modulus of elasticity E_L . The longitudinal stiffness and acoustic velocity in the longitudinal direction has been related to a range of wood properties such as the microfibril angle (MFA),^{43–47} tracheid dimensions,⁴⁸ and density.^{46,49–54} Huang *et al.* provides a review on this topic and its relationship to the acoustic velocity in wood.⁵⁵ In general, longitudinal stiffness, and hence longitudinal velocity, increases with reduced MFA and increased density. However, some studies have cautioned against using density alone as a measure of MOE^{56,57} or have reported no correlation of MOE and density.^{58,59}

B. Relationship between mechanical properties and speed of sound in wood

1. Dilatational (bulk) waves in wood

The orthotropic nature of wood means that the speed of sound depends on the direction of propagation. The sound speed in the longitudinal orthotropic axis direction is the highest, while that in the tangential axis direction is the lowest (see Fig. 3).^{24,47} Also, the acoustic attenuation is lowest in the longitudinal direction.⁶⁰ This attenuation is significantly higher than steel, for example, and increases with frequency.⁶⁰ These factors mean that the first arrival of an acoustic signal tends to follow the wood grain.^{61–66}

The velocity of an acoustic signal in a medium for a particular direction is related to the medium's mechanical properties. This may be described by the Kelvin-Christoffel equation

$$\begin{bmatrix} \Gamma_{11} - \rho c^2 & \Gamma_{12} & \Gamma_{13} \\ \Gamma_{12} & \Gamma_{22} - \rho c^2 & \Gamma_{23} \\ \Gamma_{13} & \Gamma_{23} & \Gamma_{33} - \rho c^2 \end{bmatrix} \begin{bmatrix} p_1 \\ p_2 \\ p_3 \end{bmatrix} = 0, \quad (6)$$

where Γ_{ik} is the Kelvin-Christoffel matrix, p_m is a polarization vector, which indicates the direction of vibration, and ρ is the density.⁶⁷ For an orthotropic medium,

$$\begin{aligned} \Gamma_{11} &= n_1^2 C_{11} + n_2^2 C_{66} + n_3^2 C_{55}, \\ \Gamma_{22} &= n_1^2 C_{66} + n_2^2 C_{22} + n_3^2 C_{44}, \\ \Gamma_{33} &= n_1^2 C_{55} + n_2^2 C_{44} + n_3^2 C_{33}, \\ \Gamma_{12} &= n_1 n_2 (C_{12} + C_{66}), \\ \Gamma_{13} &= n_1 n_3 (C_{13} + C_{55}), \\ \Gamma_{23} &= n_2 n_3 (C_{23} + C_{44}), \end{aligned} \quad (7)$$

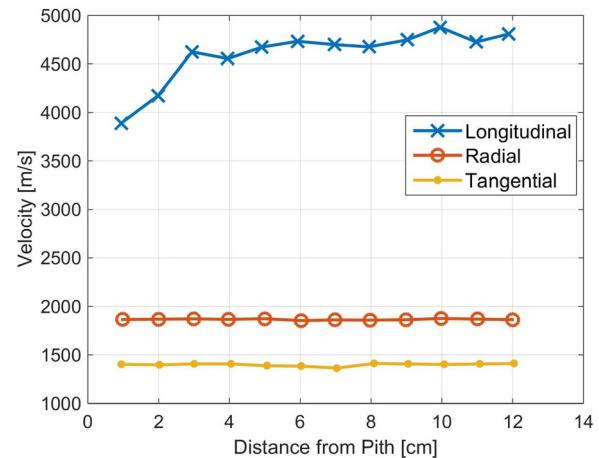


FIG. 3. (Color online) Figure reproduced from Ref. 47 showing variations in the acoustic velocities in three orthotropic directions for Japanese cypress as a function of distance from the centre of the tree (pith).

where n_j are propagation direction cosines. This equation can be used to calculate the velocity of shear and compressional dilatational (bulk) waves in different propagation directions relative to the orthotropic axes.^{68–75} Other models, including the Hankinsen's model, have been proposed for the speed of sound in wood as a function of grain angle in the radial/tangential^{76–78} and longitudinal⁷⁹ directions.

The Kelvin-Christoffel equation can be used to calculate the theoretical speed of an acoustic dilatational wave (in an infinite unbounded medium). The speed of a wave propagating along the longitudinal orthotropic axis may be calculated, using $n_1 = 1$ and $n_2 = n_3 = 0$, as

$$c_L = \sqrt{\frac{C_{11}}{\rho}} = k \sqrt{\frac{E_L}{\rho}}, \quad (8)$$

where k is a term greater than one that is related to the Poisson's ratios of wood. For an orthotropic medium, the Kelvin-Christoffel equation gives

$$k = \sqrt{\frac{1 - \nu_{RT}\nu_{TR}}{1 - \nu_{RT}\nu_{TR} - \alpha}}, \quad (9)$$

where $\alpha = 2\nu_{RL}\nu_{TR}\nu_{LT} + \nu_{TL}\nu_{LT} + \nu_{RL}\nu_{LR}$. Refer to Sec. 4.1 of Ref. 24 and Sec. 1.3 of Ref. 67 for more details. Note that if all six Poisson's ratios were equal (a single Poisson's ratio), one would get the isotropic case

$$k = \sqrt{\frac{(1 - \nu)}{(1 + \nu)(1 - 2\nu)}}. \quad (10)$$

Equation (8) provides a theoretical dilatational wave speed in an unbounded medium (in the longitudinal direction).

The acoustic velocity in wood also varies with moisture content (MC), which may change with the season of the year.^{47,80–90} The longitudinal velocity has been reported to reduce with increased MC, while the radial and tangential velocities may vary (decrease and increase) as MC was varies.⁸³ In addition, the density of wood increases with MC. Both these factors will have an effect on the measured MOE obtained using acoustic techniques.⁸⁷ Corrections for moisture content in MOE calculations using acoustic velocity have been investigated by several authors.^{86,89} Temperature also influences the acoustic velocity in wood.^{82,86,88,91–96} The velocity decreases with increased temperature. There is an abrupt change in velocity around the freezing point.^{97–100}

2. Rod waves in tree stems

An acoustic signal initially propagates in a log as bulk or dilatational waves.^{101,102} The first arrival times for a 3D stress wave propagating through a tree stem has been investigated experimentally in several papers.^{103–106} Searles reported that the first arrival times could initially be explained by elliptical wave fronts, with the semi-axes being obtained from the orthotropic velocities in the longitudinal and radial directions.¹⁰⁶ Zhang *et al.* states that the first arrival wave fronts become approximately planar after the

wave has propagated about ten stem diameters from the impact point on the side of the trunk.¹⁰³ It is generally assumed that after propagating sufficient distance the first arrival of this compressional wave in the tree stem becomes a 1D "rod wave" with a velocity of^{20,101,102,107}

$$c_L = \sqrt{\frac{E_L}{\rho}}. \quad (11)$$

This equation is used to calculate the elastic modulus E_L of a tree stem from measurement of the acoustic velocity. Generally a fixed density is assumed for a given tree type. For example, the density of radiata pine is often chosen to be about 1050 kg/m³. This can lead to errors in the calculated MOE values since the actual density of the tree stem may be different to this assumed value and will vary within the tree stem. However, generally errors in velocity are considered to be the main source of error in MOE values, since the dynamic MOE is proportional to the square of velocity. It should be noted, however, that Eq. (11) is an approximation of one type of vibration in a isotropic, homogeneous, thin rod.¹⁰⁸ Tree stems, however, are actually orthotropic, non-homogeneous, and have a finite diameter and a taper. This has the potential to lead to errors in stiffness measurement.

3. Acoustic/ultrasonic guided waves in tree stems

Waves which propagate along tree stems are often referred to as "rod waves." However, these appear to be what are more generally referred to as acoustic guided waves. An elongated structure such as a rod or plate acts as a wave-guide for an acoustic signal if the diameter of the structure is approximately proportional to the wavelength of the signal. The signal initially propagate as dilatational (bulk) waves. However, after propagating sufficient distance, guided waves will be generated, which would be expected to be composed of multiple wave modes. For a rod like structure, these would be longitudinal, flexural, and torsional wave modes. These propagate at different speeds and are generally dispersive; having wave speeds, which vary with frequency and diameter of the structure. For example, if the diameter of a steel rod (or plate) was reduced, the velocity of a longitudinal wave mode at a given frequency would be expected to change. Also, the number of wave modes that can propagate for a given frequency range might change with the diameter.

The study of acoustic/ultrasonic guided waves is well established for homogeneous materials such as metal pipes, rod, and plates and some anisotropic materials such fiber glass or carbon fiber sheets.^{109–112} For objects with simple geometries, such as steel plates and rods, commercial software has been developed for obtaining the phase and group velocities as a function of frequency (dispersion curves). For objects with more complex geometries, finite element analysis (FEA) software may be used.

For tree stems, the high anisotropy and inhomogeneity of wood make the wave propagation more complex than in homogeneous, isotropic materials such as steel rods. Only a few studies were found which had investigating guided

waves in timber^{113,114} or logs.^{115–118} There have been several other papers that have described guided wave phenomena, though have not specifically referred to them as being due to guided wave effects. Marra *et al.* stated that, as the dimensions of a piece of timber approach the wavelength of the acoustic signal, the velocity becomes a function of wavelength and these dimensions.¹¹⁹ Others have also reported the acoustic/ultrasonic wave velocity in timber being dependant on the frequency and dimensions of the timber.^{24,77,119–123} The complex signals measured in wood have been attributed by some as being due to different modes or dispersion, though little detail has been provided. Generally only the first arrival time of the signal is measured while the remainder is ignored. This complex signal following the first arrival may be the result of different guided wave modes. More research in this area is needed.

C. Additional factors affecting acoustic velocity in tree stems

Variations in stiffness, density, and MC within a tree can affect the acoustic velocity. The longitudinal MOE and the density of a log, when dried, increases from pith outward toward the bark (see Fig. 4).^{56,124} However, this effect is offset to some degree by the higher moisture content at the core of the log than in the outerwood. This results in the longitudinal wave velocity increasing from pith to bark,^{45,47,49,124,125} though not as much as might be expected from dry wood density alone.¹⁰⁷ The acoustic velocity is also reported to decrease with height up the tree stem.^{57,126–129} However, some studies have reported that the longitudinal acoustic velocity in radiata pine initially increased to a maximum a few meters up the tree and then decreased with height.^{107,126,130}

Reaction wood within the tree stem can also cause variations in acoustic velocity measurements.¹³¹ Also, variations in grain angle, including knots/branches and spiral grain, can reduce the measured velocity observed in wood.^{58,106,126,132–136} Gerhards showed that the wave front of an acoustic signal tends to follow the grain and flow

around knots, potentially resulting in measurements of reduced acoustic velocity.¹³³

Acoustic velocity has also been reported to have a negative correlation with diameter at breast height (DBH), for the same age of tree.^{137,138} Some have stated that this correlation of DBH and stiffness, and hence velocity, can be inconsistent due to variations in growth rates between different locations. Instead it is suggested that tree stiffness should be compared against stem slenderness (taper), which is the ratio of height/DBH. A strong correlation of slenderness with stiffness has been reported for mature^{1,50,59,139–142} and juvenile^{143,144} trees. This increased stiffness with the slenderness has been suggested as being a natural mechanism to prevent buckling of tree stems.¹⁴⁵ Wind exposure appears to have an effect on the stiffness of trees.¹ Also, the acoustic velocity increases with the age of the tree.^{58,124,146–148} Auty and Achim¹⁴⁶ proposed a non-linear model

$$E_L(\text{age}) = \beta_1 \left[\frac{\text{age}}{\beta_2 + \text{age}} \right] + \beta_3, \quad (12)$$

to take into account the effect of age on MOE for Scots pine. Similar models are provided in reference.¹⁴⁹ Gonçalves *et al.* reported that the rate of acoustic velocity increase with age for *Pinus elliottii* was highest in younger trees.¹⁴⁷

III. MEASUREMENT OF THE STIFFNESS OF WOOD USING ACOUSTIC SENSORS

Acoustic NDT techniques have been developed to estimate the longitudinal modulus of elasticity (often referred to as the dynamic modulus of elasticity), E_L , of standing trees and logs. This is achieved by exciting stress waves in the tree stem and measuring the velocity c_L in the longitudinal direction. The dynamic MOE of a tree stem is calculated from Eq. (11) using the measured acoustic velocity and the wood density.²⁰ There are two methods used to measure acoustic velocity; acoustic resonance and time of flight (TOF).

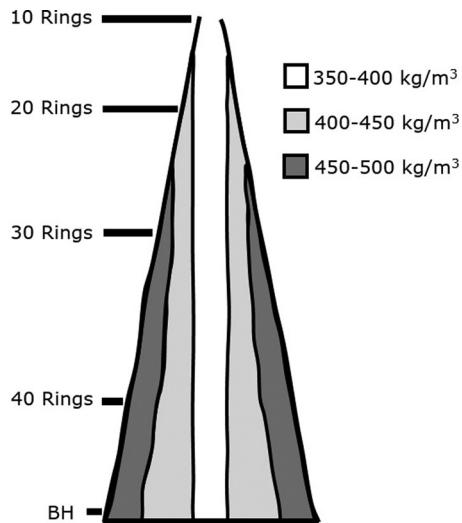


FIG. 4. Figure reproduced from Ref. 131 showing within tree variation in air dry density for radiata pine.

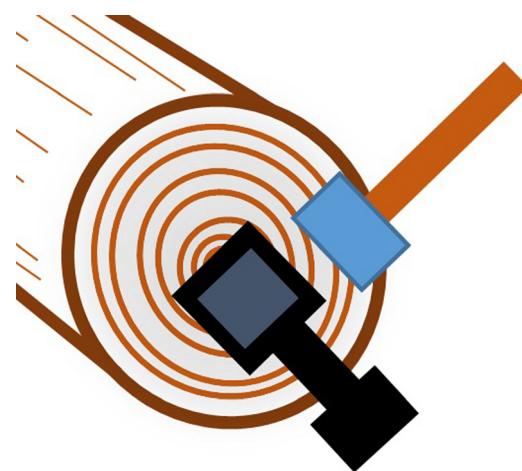


FIG. 5. (Color online) Diagram of an acoustic resonance tool used for measuring the acoustic velocity in logs.

A. Acoustic resonance tools for measuring the stiffness of logs

Transverse vibration techniques have been developed for measuring the stiffness of lumber, which use transverse vibrations generated by an impact near the middle of the sample.^{108,119,150–153} The longitudinal vibration technique, however, is more common and is used for measuring the stiffness of both logs and lumber. It utilizes vibrations, which are predominantly in a direction parallel to the grain of the wood. Longitudinal stress waves are generated by an impact from a hammer or similar object at one end of the log or timber (see Fig. 5). The resulting stress waves are reflected from each end of the log many times and standing waves are generated. The signal is recorded and a fast Fourier transform (FFT) of the signal is obtained. The frequencies at which peaks occur in the signal are measured. The longitudinal acoustic velocity may be calculated from the n th resonance frequency f_n using

$$c_{\text{RES}} = \frac{2Lf_n}{n}, \quad (13)$$

where L is the length of the log. Early work using resonance for measuring the stiffness of logs was performed in Japan.^{154–158} Harris *et al.*¹⁵⁹ and Lindstrom *et al.*¹⁶⁰ used an alternative technique for exciting resonance. Rather than using a hammer hit, a transducer and a chirp signal (swept frequency) were used to generate longitudinal resonance.

Acoustic resonance tools have been developed for sorting logs in sawmilling installations.¹⁶¹ A study on the potential of resonance based tools for installation on a harvester head is provided in Refs. 162 and 163. However, the need for knowing the length of the log before calculating the MOE appears to limit the practical use of resonance for harvester head application. Acoustic resonance measurements have also been made for seedlings or juvenile trees.^{12,160}

1. Example commercial acoustic resonance hardware

There have been a number of hand held resonance tools for measuring the acoustic velocity in logs. Fibre-gen¹⁶⁴ have developed the HITMAN HM200.^{165–167} This is a newer version of the Director HM200 provided by Carter Holt Harvey fibre-gen. Achim *et al.* provides a description of the design of a hand-held longitudinal resonance tool.¹⁶⁷ Fakopp¹⁶⁸ have a similar tool referred to as Resonance Log Grader.¹⁶⁹ Fiber-gen have developed the HITMAN LG640 for sorting logs in sawmilling installations.¹⁷⁰ There have also been a range of production line acoustic resonance tools for measuring the stiffness of lumber.^{171–173}

2. Acoustic resonance tool errors

Studies have shown that there is a strong correlation between the MOE values calculated using the acoustic resonance technique and those obtained using mechanical bending of boards^{34,44,127,159,160} (see Fig. 6). It has been suggested this technique provides MOE measurements, which are an average through the cross-section of the log.^{124,159,174} This has been associated with the fact that it

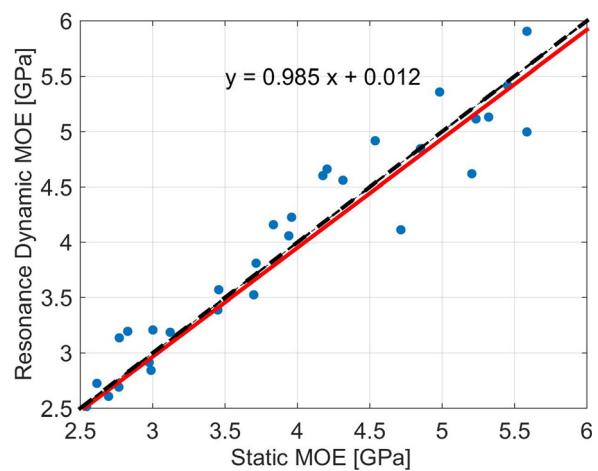


FIG. 6. (Color online) Correlation between the static (bending) and dynamic (resonance) modulus of elasticity. Figure reproduced from Ref. 160.

uses an acoustic signal that has propagated many times through the length of the log due to multiple reflections from each end. However, there are a few factors that have been suggested as potential sources of errors in resonance measurements.

There has been some discussion on the optimal way of exciting resonance in logs. In a paper describing their swept frequency resonance device, Harris *et al.* raises questions of the potential for errors for resonance devices that use hammer hits.¹⁵⁹ They performed time frequency analysis of the signal induced by hitting the end of a log with a hammer. The resonant frequencies varied with time but the overall spectrum was dominated by the first few reverberations due to attenuation. It was also questioned whether a hammer hit is the optimal way of exciting resonance. Andrews suggests there is the potential for the resonance frequencies of the log to be outside the main frequency components generated by the hammer hit (mainly around 1 kHz for wet logs).¹⁷⁵ It should be noted, however, that Chauhan and Walker provides a comparison of acoustic velocities obtained using two different resonance devices, which excite the logs using either a hammer hit or a frequency sweep transducer (Hitman HM300 and WoodSpec), and a good correlation was observed.⁵⁸

Some studies have looked at which harmonic should be used for resonance measurements. Andrews reported that the measured resonance peaks may not be harmonics of each other.¹⁰⁷ He stated that the taper of the tree can affect the resonance frequency, particularly for the lower frequency vibration. Chauhan and Walker reported that the acoustic velocity measured using the first and second harmonic can vary by as much as 11%.⁵⁸ It was suggested that the second harmonic was more accurate and appeared to be that used by Hitman HM300. The location of knots may also affect some resonance frequencies.^{58,135}

The presence of bark on a log can cause errors in acoustic velocity measurements using resonance techniques. Lasserre *et al.* reported that removing the bark on a tree stem increased the resonance velocity measured MOE value by 8% on average.¹⁷⁶ Similarly, Hsu reported that bark removal

increased the acoustic velocity by 7.2% for logs from the base of the tree.¹²⁶ This effect increased with height in the tree, with a maximum of 22.6% near the top. This appears to be related to the fact that the proportion of bark to wood mass increased with height. A similar increase in velocity with bark removal was observed by Emms *et al.* for juvenile trees.¹⁷⁷ The increase in sound speed reported in these references ranged from 3% to 22%.

The presence of branches on a log has also been reported to cause errors in the acoustic velocity measured using resonance. Lasserre *et al.* found that removing branches increased the measured MOE obtained using resonance by on average 5.4% but this value varied from 24% to 0%.¹⁷⁶ Similarly, in a study on the potential of the using resonance for harvester head segregation, Amishev also observed an increase in resonance velocity with removal of branches for Douglas fir.¹⁶³

3. Damping measurement from acoustic resonance data

Acoustic resonance raw data obtained using a hammer hit can be analyzed to obtain more information on wood properties, such as damping. Damping can be measured in the time domain from the rate that the signal amplitude drops off with time. In the frequency domain, it has been related to the narrowness of the resonance peaks. This can be expressed as a Q-factor using

$$Q = \frac{f_c}{f_2 - f_1}, \quad (14)$$

where f_c is the central frequency of the resonance and f_1 and f_2 are upper and low frequencies where the peak has dropped a certain amount (perhaps -3 dB) below the peak. The Q factor can be related to a damping factor $\xi = (2Q)^{-1}$. Damping will vary with frequency due to the fact that higher frequencies experiencing more attenuation rates.¹³⁵ This is likely to be the cause of the change in resonance peak frequency with time that Harris *et al.* observed¹⁵⁹ and may influence the resonance frequencies obtained using acoustic resonance. Damping has been relating by several studies to the stiffness of wood.^{135,178} However, damping measurements do not appear to be commonly used for wood stiffness evaluation and is more commonly used for detecting rot in tree stems.^{179–184}

B. Acoustic time of flight tools for measuring the stiffness of standing trees

The stiffness of standing trees cannot be measured using the acoustic resonance technique, since this method requires two cut ends. Instead the stiffness of standing trees may be estimated by measuring the acoustic velocity in the stem using TOF techniques. TOF velocity measurements are generally made using stress waves excited by an impact from a hammer on a metal spike inserted into a tree stem.^{185,186} Two spikes/probes are generally inserted on the same side of the tree (“same face”), which are separated vertically by about a meter. They are usually orientated at an angle of 45°

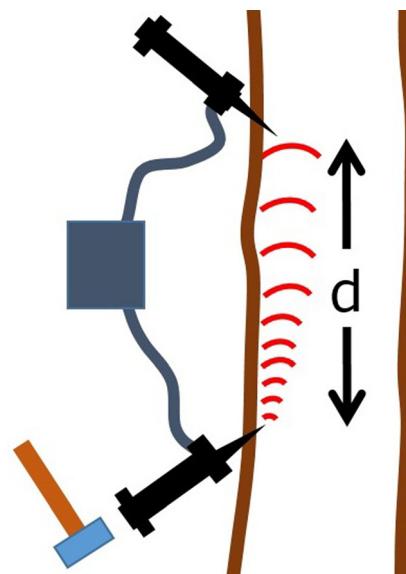


FIG. 7. (Color online) Diagram of an acoustic TOF tool used to measure the velocity in standing trees.

to the stem with the tips facing each other. One probe is hit with a hammer and the time T that it takes for the stress wave to first reach the second probe is measured, see Fig. 7. The acoustic velocity is then calculated using

$$c_{\text{TOF}} = \frac{d}{T}, \quad (15)$$

where d is the separation between probes. A description of a design of this type of TOF tool can be found in the patents.^{187,188} An slightly different measurement technique was used by Toulmin and Raymond¹⁸⁹ and Woods¹⁹⁰ who used three probes: one for hitting with a hammer and the other two for receiving. A harvester head TOF device has recently been developed.¹⁹¹ TOF velocity measurements have also been performed using ultrasonic transducers instead of a hammer hit.^{192–194}

It has been reported that TOF methods overestimate the stiffness compared to bending and resonance techniques (see Sec. IV). An alternative technique has, therefore, been tried that has the transmit and receive probes on different sides (“opposite faces”) of the tree, with the probes separated vertically by about a meter.^{195–200} This was performed to try to measure an average stiffness through the entire tree stem. Mahon¹⁹⁹ and Mahon *et al.*²⁰⁰ investigated different propagation paths through the tree stem to allow for variations in the diameter of the tree when calculating the TOF velocity. A problem that has been reported with this technique was that the results underestimated the MOE. This appears to be due to the fact that these studies have not allowed for the anisotropy of the wood, where the velocity in the radial direction is significantly lower than in the longitudinal direction.

A few studies have used the TOF technique to measure the stiffness on logs. This generally involves using a hammer hit^{201–210} or an ultrasonic transducer²¹¹ to generate an acoustic signal at one end of a log, and measuring the TOF to the other end of the log. However, this technique is rarely used for measuring the stiffness of logs since it is considered to be

less accurate than acoustic resonance techniques and leads to an overestimation of stiffness. TOF acoustic velocity tools have also been developed for measurements of the stiffness of seedlings and juvenile trees in breeding studies.^{12,160,212} Emms *et al.* developed a technique for measuring the TOF acoustic velocity in seedlings using cross-correlation of the signals measured on two spatially separated sensors using a pinhead strike as a sound source.^{177,213}

1. Example commercial acoustic TOF hardware

Many of the TOF tools are composed of two probes and a hammer. A description of the design of this type of TOF tool can be found in the patents.^{187,188} Commercial versions of this tool is the produced by Fibre-gen¹⁶⁴ in the form of the HITMAN (Director) ST300. A harvester head version of the ST300 is the HITMAN PH330.²¹⁴ Other commercial hand held tools include the TreeSonic and Fokopp 2D,^{202,215} which were developed by Fakopp,¹⁶⁸ Metriguard,^{216,217} and IML Micro Hammer.²¹⁸

There have also been several tools which use ultrasonic excitation to measure the acoustic velocity in trees and logs. These include Fokopp's Ultrasonic Timer,²¹⁹ Agricef USLab,²²⁰ CBS-CBT Group's Sylvatest Duo and Sylvatest Trio,^{192,193,221} and an ultrasonic device produced by the University of Canterbury.¹⁹⁴ The Krautkramer USD10-NS Ultrasound flaw detector²²² is referred to in Ref. 12. There have also been a range of production line ultrasonic TOF tools used for grading of lumber^{173,193,223,224} and veneer.^{225,226}

2. Acoustic TOF tool errors

Studies have shown that there is a good correlation of stiffness measurements made using the TOF technique and other methods, such as bending and resonance. TOF velocity measurements, however, are considered be less accurate than those obtained using the acoustic resonance technique. As will be discussed in Sec. IV, TOF techniques produce stiffness measurements that are overestimated compared to those obtained using acoustic resonance and bending techniques. Also, the fact that signal used in the TOF technique has propagated a relatively short distance (about a meter) compared to that used for resonance (many reflections from the ends of log), has been attributed to TOF measurements being more sensitive to errors resulting from local inhomogeneity in the wood properties and measurement errors. Variations in grain angle, including that due to knots/branches and spiral grain, can reduce the measured TOF velocity observed along a tree stem.^{58,106,126,132–136} Reaction wood and non-symmetric variation in stiffness within the tree stem can also cause variations in acoustic TOF measurements. To compensate for these effects, multiple measurements may be made at different points around a tree to try to obtain an average velocity measurement.^{176,227} Variations in results have also been reported with individual hammer hits. This can be compensated for by averaging over multiple measurements.⁴¹

Several studies have provided data that appear to indicate that TOF velocity measurements are more closely correlated with outerwood MOE than that of the corewood.

Grabianowski *et al.* made TOF measurements of lumber at different positions in logs.¹²⁴ They found that TOF acoustic velocity measurements had a higher correlation to resonance velocities in the outerwood than in the corewood. Chauhan and Walker state that their TOF measured MOE values were more correlated with SilviScan MOE measurements than that obtained using resonance.⁵⁸ Mora *et al.* also compared TOF calculated MOE values with those made using a SilviScan at different depths in the tree.²²⁸ They reported that the difference in the MOE values increased with depth from the bark. A similar result was obtained by Hong *et al.*²²⁹ Paradis *et al.* reported that the measured TOF acoustic velocity can vary with the depth that the probes are inserted into the tree stem.²³⁰

IV. SYSTEMATIC DIFFERENCE BETWEEN TOF AND RESONANCE

Studies have found that the TOF method provides measured values of MOE which are higher than those obtained using resonance for standing trees and logs^{58,101,124,126,127,176,228,231–233} (see Fig. 8). Wang provides a review on this topic.⁴¹ The overestimation of TOF compared to resonance velocity has also been reported to occur even if the TOF velocity measurements were made from pith to pith at each end of the log.^{126,209} Yin *et al.*²³² and Chiu *et al.*¹²⁷ reported that dynamic MOE values obtained using both TOF and resonance were higher than static MOE calculated using bending tests, though the resonance value was closer to the static values.

The higher TOF velocity compared to resonance velocity has been expressed as the ratio

$$k = \frac{\overline{c}_{\text{TOF}}}{\overline{c}_{\text{RES}}}, \quad (16)$$

where $\overline{c}_{\text{TOF}}$ is the average TOF velocity measured in trees and $\overline{c}_{\text{RES}}$ is the average resonance velocity measured in logs. The individual resonance and TOF velocity data points have been fitted by many using

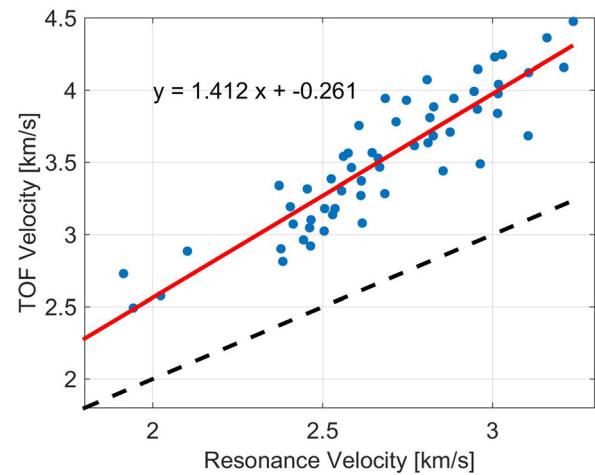


FIG. 8. (Color online) Figure is reproduced from Ref. 228 showing overestimation of TOF in standing trees compared to resonance velocity in logs cut from the trees.

$$c_{\text{RES}} = a + b c_{\text{TOF}}, \quad (17)$$

which is the same as Eq. (16) if $a=0$ and $b=1/k$. A range of studies have investigated the overestimation of TOF compared to resonance for radiata pine in New Zealand.^{58,101,124,126,176,234} They show some variability in the fitted parameters a and b and provide k values which ranged from 1.07 to 1.31 with a mean of about 1.15.

The diameter of a tree has been reported by some papers to have an effect on the overestimation of TOF velocity c_{TOF} in standing trees compared to bending¹³⁸ and resonance.^{58,101,138} An empirical multi-variable model, developed by Wang *et al.*,¹³⁸ models the resonance acoustic velocity in a tree stem in terms of the TOF velocity as

$$c_{\text{RES}} = a \left(\frac{\text{DBH}}{\rho} \right)^b c_{\text{TOF}}^g, \quad (18)$$

where DBH is the diameter at breast height, a , b , and g are least squares fitted parameters, and ρ is the density and would reduce to Eq. (16) if $a=1/k$, $b=0$, and $g=1$. This was used to provide an empirical correction for TOF data.^{102,138,234} Chauhan and Walker noted that the difference between TOF and resonance velocities tended to be greater in the older and larger diameter trees.⁵⁸ A few studies, however, have reported not observing any significant effect of diameter on the difference between TOF and resonance.^{176,228} Gonçalves *et al.* looked at several tree species and reported that the dependence on tree diameter was only observed for some of these species.²³³

Several papers have stated that the presence of bark on a tree stem can cause the measured resonance velocity on a log to be lower than it would be without bark and thereby cause an underestimation of the MOE of a log. The presence of bark on logs has, therefore, been attributed to causing the measured value of k to be higher than it should be.^{58,124,176} It was reported by Lasserre *et al.* that values of MOE obtained using resonance measurements with and without bark were, respectively, on average 38% and 33% lower than MOE values obtained using TOF with the bark on the tree stem.¹⁷⁶

A. Explanations for the overestimation of TOF compared to resonance and corrections

There have been several explanations provided in the literature on the reason for the overestimation of TOF compared to resonance and some corrections. This section provides a review of these explanations.

1. Viscoelastic properties of wood explanation of TOF overestimation

It has been suggested that the higher MOE values compared to resonance and bending are related to the viscoelastic nature of wood.^{235,236} Static bending was considered to be a vibration with a very low frequency. Therefore, static bending, resonance, and ultrasound were regarded as three forms of vibration with, respectively, three increasing levels of vibrational frequencies. Increased MOE measured values obtained with the three different techniques were related to

an increase in velocity with increased frequency (dispersion). Ouis reviewed this idea and provided mathematical models.²³⁶

2. Variation in stiffness from pith to bark explanation

The longitudinal stiffness of wood increases from pith to bark. It has been assumed that the resonance technique provides an average stiffness measurement through the entire cross-section of the tree stem. In contrast, it is suggested that the TOF technique provides results which are biased toward outerwood MOE.^{58,126,138,176} Hsu suggested that the fact that TOF velocity measurements, which were made from pith to pith at opposite ends of logs, were still higher than that obtained using resonance, was because the fastest propagation path would involve the acoustic signal propagating in the stiffer outer-wood for some part of the travel time.¹²⁶ Chauhan and Walker assumed that the overestimation with diameter was due to the oldest stands and larger diameter trees having a large difference in stiffness between outerwood and corewood.⁵⁸

Some studies have performed TOF and resonance tests on timber samples. These studies also reported that the velocities obtained using TOF were higher than those obtained using longitudinal resonance^{237–239} and flexural resonance.^{235,237,240,241} Others have reported that TOF measured dynamic MOE values for timber samples were higher than static MOE values calculated using bending tests on these samples.^{185,186,208,235,237,242,243} Hassan *et al.* reported that dynamic MOE obtained using flexural vibration, longitudinal vibration, and ultrasound (TOF) were greater than those of static MOE values by 13.8, 22.3, and 30.9%, respectively.²³⁹ Similar results were reported by Yang *et al.*²³⁷ Searles measured TOF velocity for stress wave propagation along a thin billet cut from a log.¹⁰⁶ He reported that a reduction in velocity was observed with propagation distance. He proposed that the overestimation of TOF compared to resonance was related to boundary effects and not due to changes in material properties.

3. “Bulk” and “rod” velocity explanation

An explanation of the difference between TOF and resonance is related to the wave propagation through the log. For the TOF technique, the effective propagation distances are typically only about a meter, while for resonance the propagation distance may be many lengths of the log. Andrews¹⁰¹ and Wang *et al.*^{102,234} suggested that, for the TOF velocity measurement technique, the acoustic signal will propagate at a “dilatational” speed. Assuming an infinite, unbounded, isotropic medium, they give this dilatational speed as

$$c_{\text{TOF}} = \sqrt{\frac{C_{11}}{\rho}} = \sqrt{\frac{(1-\nu)}{(1+\nu)(1-2\nu)}} \sqrt{\frac{E_L}{\rho}}, \quad (19)$$

coming from Eqs. (4), (5), (8), and (10), where ν is the Poisson’s ratio. However, for the acoustic resonance technique, where the acoustic waves have propagated a significant distance involving many reflections from the ends of

the log, they assumed that the signal propagates at a “rod” speed [see Eq. (11)]

$$c_{\text{RES}} = \sqrt{\frac{E_L}{\rho}}. \quad (20)$$

It is, therefore, suggested that the overestimation of TOF compared to resonance is given by the ratio of Eqs. (19) and (20) giving

$$k = \frac{c_{\text{TOF}}}{c_{\text{RES}}} = \sqrt{\frac{(1-\nu)}{(1+\nu)(1-2\nu)}}. \quad (21)$$

For example, Wang *et al.*¹⁰² observed that the TOF velocity for Sitka spruce was 1.22 times that for resonance and used Eq. (21) to calculate an isotropic Poisson’s ratio of 0.331.

For TOF measurement in trees, it is suggested that the wave propagation is dominated by dilatational waves and that this effect increases with diameter causing the higher velocity for TOF compared to resonance. The MOE values obtained using TOF for standing trees were corrected for this dilatational speed effect using

$$E_L = \left(\frac{c_{\text{TOF}}}{k}\right)^2 \rho, \quad (22)$$

where k was determined from experimental measurements from trees of the same species.^{41,102,234,244} It was reported that the corrected TOF dynamic MOE values were well correlated with those obtained using resonances. This method requires a calibration data set of TOF and resonance velocities for calculating k . Since factors such as age, DBH, and genome type has been reported to influence the overestimation k , a range of different calibration data sets might be beneficial.

Mora *et al.*²²⁸ extended Eq. (22) to include a correction for the effect of moisture content on density

$$E_L = K \left(\frac{c_{\text{TOF}}}{k}\right)^2 \times \rho \left\{ 1 - \frac{(1-k)(MC - MC_{\text{FSP}})}{100 + MC} \right\}, \quad (23)$$

where MC is the moisture content (%), MC_{FSP} is the moisture content at fiber saturation (30% is used), κ is the mobility of free water (0.6 is used), and K is a constant 9.84×10^{-10} used to incorporate gravitational acceleration and conversion constants to express stiffness in GPa. They reported that including the moisture content correction resulted in improved dynamic MOE values, which compared well with static MOE values obtained using bending tests. Other studies that have investigated correction of MOE values for moisture content can be found in Refs. 86 and 89.

B. Discussion

Most of the studies comparing TOF measurements on trees with resonance measurements on felled logs have generally only compared TOF and resonance velocities. Only a few of the studies have provided comparison with other

techniques. Generally this comparison was only made with TOF measurements and not those obtained using resonance. It would be beneficial if any future studies on this topic included more comparisons with other techniques, such as static bending tests, and made this comparison with resonance as well as TOF. Also, ideally these studies would include measurements made with the bark and branches removed from the felled logs before making the resonance tests, since these have been shown to cause errors in resonance measurements. Future studies could also compare k measurements with tree slenderness (tree height/DBH), since this characteristic of trees has been reported to have a strong correlation with stiffness.^{1,50,59,139–144}

One of the ideas to explain the higher TOF measurements compared to resonance is variation from pith to bark of the tree stem. Several studies have reported that MOE values obtained using TOF techniques have higher correlation with outerwood MOE than that closer to the pith. However, other studies have reported that the overestimation also occurs in thin timber samples. This appears to indicate that the variation in stiffness may contribute to, but probably is not the main mechanism of, the overestimation.

Andrews¹⁰¹ and Wang *et al.*^{102,234} suggested that the TOF method measures the dilatational (bulk) wave speed, while the resonance technique measures the “rod” speed of the log. Equation (21) was used to explain the overestimation of TOF compared to resonance and provide TOF corrections.^{102,234} This appears to be a good explanation for the overestimation. However, Eq. (21) uses isotropic wave propagation theory with a single Poisson’s ratio, while wood is an orthotropic material and has six Poisson’s ratios. Equation (9) provides an orthotropic version of Eq. (21). Using the six orthotropic Poisson’s ratios for Sitka spruce given in Table I, a theoretical value of $k = 0.02$ is obtained. Because of the low values of ν_{RL} and ν_{TL} , this value is significantly smaller than the measured overestimation of $k = 1.22$ reported by Wang *et al.*¹⁰² for Sitka. It is possible that the orthotropic Poisson’s ratios used are not correct (ν_{RL} and ν_{TL} are usually not measured) or that Eq. (9) does not accurately represent the wave propagation. More work on this topic, incorporating the orthotropic nature of wood, would be beneficial.

It is likely that the signals used by resonance are guided waves. Could the variation in overestimation of TOF with diameter be related to a guided wave effect? Also, could dispersion be playing a role? The longer propagation distance for the signals used for resonance means that more of the higher frequency components of that signal will have been filtered out compared to TOF. Could different frequency components in the signal be propagating at different speeds? It may be that more work on guided waves in tree stems may provide improved understanding of the difference between TOF and resonance velocity and potentially more accurate stiffness measurements.

V. OTHER TECHNIQUES COMBINED WITH ACOUSTIC TOOLS FOR MEASURING STIFFNESS

The use of other techniques with acoustics has been investigated for increasing the accuracy of stiffness

measurements. Wang *et al.* reported that, for Douglas fir, the combination of log diameter or log position (height) in the tree with longitudinal acoustic velocity were better predictors of average lumber MOE and visual grade yield than log acoustic velocity alone.¹²⁹ Acoustic velocity has been reported to be related to slenderness (height/DBH).^{139,245} It has been suggested that slenderness could be used for initial sorting of timber. Laser scanning of a log's surface to automatically measure the shape of a log in saw milling plants can also be utilized to measure slenderness and knots.²⁴⁶ Ridoutt *et al.* reported that for radiata pine the inclusion of branch size with longitudinal stress wave velocity resulted in improved sorting compared to velocity alone.²⁰⁵

VI. IDENTIFYING FACTORS INFLUENCING THE STIFFNESS OF TREES

Acoustics tools have been used to try to improve the stiffness of future forests. This has been done by trying to identify silvicultural practices or environmental conditions that affect stiffness. Acoustic tools have also been used in breeding/genetic studies to try to improve properties such as stiffness of future breeding stock. This section provides a review on some of these studies.

Studies using acoustic tools have reported that the initial planting spacing can affect stiffness. Stand spacing density has been reported to be positively correlated with acoustic velocity/stiffness for radiata pine^{59,130,137,140,247,248} and Japanese cedar.²⁴⁹ It has been suggested that the correlation of stand planting density and stiffness may be related to higher density stands experiencing less wind stress.¹³⁷ Lasserre *et al.* found that close initial stand spacing (2500 compared to 833 stems ha^{-1}) significantly increased the dynamic modulus of elasticity of radiata pine from 3.4 to 4.6 GPa. It also significantly reduced MFA and ring width, while significantly increased fiber length, latewood percentage and cell wall thickness. Density and fiber width were reported to not be significantly different between spacing treatments.⁵⁹ Similar results were observed for juvenile (6 year old) trees.¹⁴³ However, others have reported not observing this increase in acoustic velocity with stand density.^{1,144,250} Watson reported that, while radiata pine show significant increase in stiffness with planting density, *Eucalyptus nitens* did not show any significant correlation. This may indicate that the effect of stocking on MOE may vary with species.¹⁴⁸

Several studies have reported that stands that were thinned were less stiff than unthinned stands.^{57,251–253} Raymond *et al.* reported that radiata pine trees growing on thinned sites were, on average, 3% lower in stiffness at each height in the stem.⁵⁷ However, Lowell *et al.* in a study on Douglas fir found no evidence to suggest that thinning reduces stiffness.¹⁴² Wang *et al.* reported that medium pruning provided higher MOE values than unpruned or heavily pruning.^{251,252} Carson *et al.* reported that trees in the unpruned 500 stems/ha treatment had larger DBH, lower outerwood density, and lower stress-wave velocity than trees in the 400 stems/ha pruned treatment.²⁴⁸ The effect of fertilizer has also been studied with mixed reported results.^{50,254}

Geographic location appears to play a role in the properties of wood. For example, Palmer *et al.* provide a map of the variation in density (related to stiffness) of radiata pine in New Zealand, where large differences can be observed with geographic location.²⁵⁵ This variation has been suggested to be related to factors such as mean air temperature, rainfall, and soil chemistry such as total soil phosphorus.⁵⁰

Genetics plays a large part in the properties of wood such as stiffness. Considerable effort is put into studies on improving the breeding stock. Acoustic techniques are, therefore, used to identify trees that have desirable characteristics such as high stiffness to be used for breeding. Many of these studies are performed on juvenile trees to enable outcomes of breeding trials to be obtained in a shorter time frame. Studies which have used acoustics to obtain stiffness measurements on juvenile trees include references.^{12,44,143,144,160,177,213,256–267} Many of these have investigated the effect of stress such as tilting or drought. Investigations using acoustic velocity for more mature juvenile trees include references.^{12,268–275}

VII. CONCLUSION

This paper provides a review on the use of acoustics for measuring the stiffness of standing trees and felled logs. The elastic properties of wood and how these relate to velocity were presented. Other factors which influence the speed of sound in wood are described. This is reported to include the type of waves, which propagate in tree stems or lumber. Variations in stiffness and acoustic velocity with location in trees were outlined. Acoustic methods and tools used to measure stiffness and their errors were discussed. Ideas on differences between tree and log acoustic measurements and potential corrections were then presented. More study on acoustic or ultrasonic guided wave in logs/tree stems could provide a better understanding of the wave propagation and potentially help to obtain improved formulas for calculating the stiffness of tree stems. Additional techniques, which can be used in conjunction with acoustics, are briefly discussed. An overview was then provided of studies relating to the effect of silvicultural practices, geographic and environmental conditions, and genetics on acoustic velocity and hence stiffness.

ACKNOWLEDGMENTS

This work was performed as part of the Growing Confidence in Forestry Future project. Funding was provided through Scion by the New Zealand Ministry of Business, Innovation and Employment and the New Zealand Forest Growers Levy Trust. The authors would like to acknowledge John Moore and Grant Emms of Scion for their help and guidance.

¹M. Grabianowski, B. Manley, and J. Walker, "Impact of stocking and exposure on outerwood acoustic properties of *Pinus radiata* in Eyrewell Forest," N. Z. J. For. **49**(2), 13–17 (2004).

²J. R. Moore, A. J. Lyon, G. J. Searles, and L. E. Vihermaa, "The effects of site and stand factors on the tree and wood quality of Sitka spruce growing in the United Kingdom," *Silva Fennica* **43**(3), 383–396 (2009).

- ³D. Cown and L. van Wyk, "Profitable wood processing-what does it require? Good wood!," *N. Z. J. For.* **49**(1), 10–15 (2004).
- ⁴G. Young, "Profitable wood processing-sawn timber needs," *N. Z. J. For.* **49**(1), 18–20 (2004).
- ⁵S. Chauhan, R. Donnelly, C.-L. Huang, R. Nakada, Y. Yafang, and J. C. Walker, "Wood quality: Multifaceted opportunities," in *Primary Wood Processing* (Springer, Dordrecht, the Netherlands, 2006), pp. 159–202.
- ⁶X. Wang, P. Carter, R. J. Ross, and B. K. Brashaw, "Acoustic assessment of wood quality of raw forest materials: A path to increased profitability," *For. Prod. J.* **57**(5), 6–14 (2007).
- ⁷R. J. Ross, "Impact of nondestructive testing and evaluation of wood products," in *17th International Nondestructive Testing and Evaluation of Wood Symposium* (University of West Hungary, Sopron, Hungary, 2011), Vol. 1, pp. 3–7.
- ⁸J. R. Moore, "Growing fit-for-purpose structural timber: What's the target and how do we get there," *N. Z. J. For.* **57**(3), 17–24 (2012).
- ⁹J. Walker, "Wood quality: A perspective from New Zealand," *Forests* **4**, 234–250 (2013).
- ¹⁰B. Gardiner and J. Moore, "Creating the wood supply of the future," in *Challenges and Opportunities for the World's Forests in the 21st Century* (Springer, New York, 2014), pp. 677–704.
- ¹¹L. E. Páques and P. Rozenberg, "Ranking larch genotypes with the Rigidimeter: Relationships between modulus of elasticity of standing trees and of sawn timber," *Ann. For. Sci.* **66**(4), 1–7 (2009).
- ¹²A. Matheson, W. Gapare, J. Ilic, and H. Wu, "Inheritance and genetic gain in wood stiffness in radiata pine assessed acoustically in young standing trees," *Silvae Genet.* **57**(2), 56–64 (2008).
- ¹³<http://www.silviscan.com/>.
- ¹⁴R. Evans, J. Ilic, and C. Matheson, "Rapid estimation of solid wood stiffness using SilviScan," in *Proceedings of 26th Forest Products Research Conference: Research Developments and Industrial Applications and Wood Waste Forum*, edited by L. Schimleck and P. Blakemore (Clayton, Victoria, Australia, 2000), pp. 49–50.
- ¹⁵R. L. Knowles, L. W. Hansen, A. Wedding, and G. Downes, "Evaluation of nondestructive methods for assessing stiffness of Douglas fir trees," *N. Z. J. For. Sci.* **34**(1), 87–101 (2004).
- ¹⁶R. Meder, A. Thumm, and D. Marston, "Sawmill trial of at-line prediction of recovered lumber stiffness by NIR spectroscopy of *Pinus radiata* cants," *J. Near Infrared Spectrosc.* **11**(2), 137–144 (2003).
- ¹⁷A. Hanhijärvi and A. Ranta-Maunus, "Development of strength grading of timber using combined measurement techniques: Report of the Combigrade-project—Phase 2," Technical Report VTT Publications 686, VTT Technical Research Centre of Finland, Vuorimiehentie, Finland (2008), 55 pp.
- ¹⁸R. Falk, M. Patton-Mallory, and K. McDonald, "Nondestructive testing of wood products and structures: State-of-the-art and research needs," in *Non-Destructive Testing and Evaluation for Manufacturing and Construction*, edited by H. doe Reis (CRC Press, Boca Raton, FL, 1989), pp. 137–147.
- ¹⁹R. J. Ross, "Nondestructive testing of wood," in *Proceedings Nondestructive Evaluation of Civil Structures and Materials* (University of Colorado, Boulder, CO, 1992), pp. 43–47.
- ²⁰R. J. Ross and R. F. Pellerin, "Nondestructive testing for assessing wood members in structures," General Technical Report FPL-GTR-70, Forest Products Laboratory, US Department of Agriculture, Madison, WI (1994), 40 pp.
- ²¹F. Beall, "Overview of the use of ultrasonic technologies in research on wood properties," *Wood Sci. Technol.* **36**(3), 197–212 (2002).
- ²²S. Kawamoto and R. S. Williams, "Acoustic emission and acousto-ultrasonic techniques for wood and wood-based composites," General Technical Report FPL-GTR-134, Forest Products Laboratory, US Department of Agriculture, Madison, WI (2002), 16 pp.
- ²³F. Divos, F. Martítegu, J. Cabo, M. Herrero, and G. González, "Course in non destructive testing of wood: Acoustics of wood," <http://www.aq.upm.es/Departamentos/Estructuras/epa/ndt05/1Treeeval/02%20Acoustics.pdf> (Last viewed April 2014).
- ²⁴V. Bucur, *Acoustics of Wood*, 2nd ed. (Springer, New York, 2006), 393 pp.
- ²⁵V. Bucur, "Acoustics of wood," in *The Thirteenth International Congress on Sound and Vibration* (Vienna University of Technology, Vienna, Austria, 2006), pp. 1–16.
- ²⁶F. C. Beall, H. Reis, A. Senalik, and M. McGovern, "Ultrasonic nondestructive evaluation of wood and wood products-past, present and future," *Pro Ligno* **9**(4), 540–546 (2013).
- ²⁷J. Hailey and P. Morris, *Application of Scanning and Imaging Techniques to Assess Decay and Wood Quality in Logs and Standing Trees* (Forestry Canada and Alberta Forest Service, Vancouver, 1987), 54 pp.
- ²⁸V. Bucur, "Ultrasonic and X-ray techniques for nondestructive evaluation of wood," <http://webistem.com/acoustics2008/acoustics2008/cd1/data/fa2002-sevilla/forumacusticum/archivos/ult03002.pdf> (Last viewed September 2014).
- ²⁹V. Bucur, *Nondestructive Characterization and Imaging of Wood* (Springer, New York, 2003), Vol. 760, 354 pp.
- ³⁰V. Bucur, "Techniques for high resolution imaging of wood structure: A review," *Meas. Sci. Technol.* **14**(12), 91–98 (2003).
- ³¹M. Nguyen, G. Foliente, and X. M. Wang, "State-of-the-practice and challenges in nondestructive evaluation of utility poles in service," *Key Eng. Mater.* **270**, 1521–1528 (2004).
- ³²R. J. Ross, R. H. White, R. F. Pellerin, X. Wang, and B. K. Brashaw, *Wood and Timber Condition Assessment Manual*, 2nd ed. (Forest Products Society, Peachtree Corners, GA, 2014), 92 pp.
- ³³V. Bucur, ed., *Delamination in Wood, Wood Products and Wood-Based Composites* (Springer, New York, 2009), 401 pp.
- ³⁴H. Bailleres, G. Hopewell, and G. Boughton, "MOE and MOR assessment technologies for improving graded recovery of exotic pines in Australia," Technical Report PNB0400708, Forest and Wood Products Australia Limited, Melbourne, VIC, Australia (2009), 85 pp.
- ³⁵B. K. Brashaw, V. Bucur, F. Divos, R. Gonçalves, J. Lu, R. Meder, R. F. Pellerin, S. Potter, R. J. Ross, X. Wang, and Y. Yin, "Nondestructive testing and evaluation of wood: A worldwide research update," *For. Prod. J.* **59**(3), 7–14 (2009).
- ³⁶L. Gao, J. Liu, and H. Xue, "Nondestructive detection of standing trees and radar wave detection," in *2010 International Conference on Computing, Control and Industrial Engineering (CCIE)* (IEEE, New York, 2010), Vol. 1, pp. 304–307.
- ³⁷C. Wessels, F. Malan, and T. Rypstra, "A review of measurement methods used on standing trees for the prediction of some mechanical properties of timber," *Eur. J. For. Res.* **130**(6), 881–893 (2011).
- ³⁸K. J. Jaywickrama, "Breeding radiata pine for wood stiffness: Review and analysis," *Aust. For.* **64**(1), 51–56 (2001).
- ³⁹K. J. S. Jaywickrama, T. Ye, R. Gupta, and M. Cherry, "Including wood stiffness in tree improvement of coastal Douglas-fir in the US Pacific Northwest: A literature review and synthesis," Technical Report Research Contribution 50, Forest Research Laboratory, Oregon State University, Corvallis, OR (2009), 95 pp.
- ⁴⁰J. Walker and R. Nakada, "Understanding corewood in some softwoods: A selective review on stiffness and acoustics," *Int. For. Rev.* **1**(4), 251–259 (1999).
- ⁴¹X. Wang, "Acoustic measurements on trees and logs: A review and analysis," *Wood Sci. Technol.* **47**(5), 965–975 (2013).
- ⁴²J. Bodig and B. Jayne, *Mechanics of Wood and Wood Composites* (Krieger Publishing, Malabar, FL, 1993), 712 pp.
- ⁴³R. Evans and J. Elic, "Rapid prediction of wood stiffness from microfibril angle and density," *For. Prod. J.* **51**(3), 53–57 (2001).
- ⁴⁴H. Lindstrom, P. Harris, C. Sorensson, and R. Evans, "Stiffness and wood variation of 3-year old *Pinus radiata* clones," *Wood Sci. Technol.* **38**(8), 579–597 (2004).
- ⁴⁵A. Krauss and J. Kúdela, "Ultrasonic wave propagation and Young's modulus of elasticity along the grain of Scots pine wood (*Pinus Sylvestris* L.) varying with distance from the pith," *Wood Res.* **56**(4), 479–488 (2011).
- ⁴⁶B. Lachenbruch, G. Johnson, G. Downes, and R. Evans, "Relationships of density, microfibril angle, and sound velocity with stiffness and strength in mature wood of Douglas fir," *Can. J. For. Res.* **40**, 55–64 (2010).
- ⁴⁷M. Hasegawa, M. Takata, J. Matsumura, and K. Oda, "Effect of wood properties on within-tree variation in ultrasonic wave velocity in softwood," *Ultrasonics* **51**(3), 296–302 (2011).
- ⁴⁸J. Raczkowski, L. Helińska-Raczkowska, and W. Molinski, "Relationship between lengthwise ultrasound transmission and tracheid length in wood of selected softwood species," *Fol. For. Pol. Ser. B* **35**, 3–12 (2004).
- ⁴⁹B. Feeney, R. Chivers, and G. Barnard, "Meso-structural considerations of ultrasonic propagation in wood," *Mol. Quant. Acoust.* **22**, 57–68 (2001).
- ⁵⁰M. S. Watt, P. W. Clinton, G. Coker, M. R. Davis, R. Simcock, R. L. Parfitt, and J. Dando, "Modelling the influence of environment and stand characteristics on basic density and modulus of elasticity for young *Pinus*

- radiata* and *Cupressus lusitanica*,” *For. Ecol. Manage.* **255**, 1023–1033 (2008).
- ⁵¹V. Vikram, M. L. Cherry, D. Briggs, D. W. Cress, R. Evans, and G. T. Howe, “Stiffness of Douglas-fir lumber: Effects of wood properties and genetics,” *Can. J. For. Res.* **41**(6), 1160–1173 (2011).
- ⁵²L. Calegari, D. A. Gatto, and D. M. Stangerlin, “Influence of moisture content, specific gravity and specimen geometry on the ultrasonic pulse velocity in *Eucalyptus grandis* Hill ex Maiden wood,” *Rev. Ciéncia Madeira* **2**(2), 64–74 (2011).
- ⁵³E. Mason, “Designing silvicultural regimes with a structural log index,” *N. Z. J. For.* **57**(2), 13–18 (2012).
- ⁵⁴P. Gomez Ribeiro, J. C. Goncalves, R. Gonçalves, R. F. Teles, and F. de Souza, “Ultrasound waves for assessing the technological properties of *Pinus caribaea* var *hondurensis* and *Eucalyptus grandis* wood,” *Maderas. Ciencia Tecnol.* **15**(2), 195–204 (2013).
- ⁵⁵C.-L. Huang, H. Lindstrom, R. Nakada, and J. Ralston, “Cell wall structure and wood properties determined by acoustics—a selective review,” *Holz Roh- Werkst.* **61**(5), 321–335 (2003).
- ⁵⁶A. Tsehaye, “Within- and between-tree variations in the wood quality of radiata pine,” Ph.D. thesis, School of Forestry, University of Canterbury, Christchurch, New Zealand, 1995, 290 pp.
- ⁵⁷C. A. Raymond, B. Joe, D. W. Anderson, and D. J. Watt, “Effect of thinning on relationships between three measures of wood stiffness in *Pinus radiata*: Standing trees vs. logs vs. short clear specimens,” *Can. J. For. Res.* **38**(1), 2870–2879 (2008).
- ⁵⁸S. Chauhan and J. Walker, “Variations in acoustic velocity and density with age, and their interrelationships in radiata pine,” *For. Ecol. Manage.* **229**, 388–394 (2006).
- ⁵⁹J.-P. Lasserre, E. G. Mason, M. S. Watt, and J. R. Moore, “Influence of initial planting spacing and genotype on microfibril angle, wood density, fibre properties and modulus of elasticity in *Pinus radiata* D. Don corewood,” *For. Ecol. Manage.* **258**, 1924–1931 (2009).
- ⁶⁰V. Bucur and F. Feeney, “Attenuation of ultrasound in solid wood,” *Ultrasonics* **30**(2), 76–81 (1992).
- ⁶¹I. Lee, “A non-destructive method for measuring the elastic anisotropy of wood using an ultrasonic pulse technique,” *J. Inst. Wood Sci.* **1**, 43–57 (1958).
- ⁶²A. Foulger, “Notes: Through-bark measurement of grain direction; preliminary results,” *For. Sci.* **15**(1), 92–94 (1969).
- ⁶³C. Gerhards, “Effect of cross grain on stress waves in lumber,” Technical Report FPL 368, Research Paper, Forest Products Laboratory, US Department of Agriculture, Madison, WI (1980), 9.
- ⁶⁴V. Bucur and J. Perrin, “Slope of grain ultrasonic measurements in living trees and timber,” *Eur. J. Wood Wood Products* **47**(2), 75–75 (1989).
- ⁶⁵V. Bucur, “Acoustic methods as a nondestructive tool for wood quality assessment,” in *Acoustics of Wood*, 2nd ed. (Springer, New York, 2006), pp. 217–239.
- ⁶⁶I. Brémaud, J. Gril, and B. Thibaut, “Anisotropy of wood vibrational properties: Dependence on grain angle and review of literature data,” *Wood Sci. Technol.* **45**(4), 735–754 (2011).
- ⁶⁷J. M. Carcione, *Anisotropic Elastic Media* (Elsevier, Oxford, UK, 2007), Vol. 38, Ch. 1, pp. 1–49.
- ⁶⁸V. Bucur and A. Perrin, “Détermination du module d’young du bois par une méthode dynamique sur carottes de sondage” (“Wood dynamical Young’s modulus determination on increment core”), *Ann. Sci. Forest.* **38**, 283–298 (1981).
- ⁶⁹V. Bucur, “An ultrasonic method for measuring the elastic constants of wood increment cores bored from living trees,” *Ultrasonics* **21**(3), 116–126 (1983).
- ⁷⁰D. Guitard and F. El Amri, “Modèles prévisionnels de comportement élastique tridimensionnel pour les bois feuillus et les bois résineux” (“Off diagonal terms of stiffness matrix of wood”), *Ann. Sci. Forest.* **44**(3), 335–358 (1987).
- ⁷¹V. Bucur and P. N. Rasolofosaon, “Dynamic elastic anisotropy and nonlinearity in wood and rock,” *Ultrasonics* **36**(7), 813–824 (1998).
- ⁷²V. Bucur and H. Berndt, “Ultrasonic energy flux deviation and off-diagonal elastic constants of wood,” in *Ultrasonics Symposium, 2001 IEEE* (IEEE, New York, 2001), Vol. 1, pp. 697–700.
- ⁷³V. Bucur, “Theory of and experimental methods for the acoustic characterization of wood,” in *Acoustics of Wood*, 2nd ed. (Springer, New York, 2006), Chap. 4, pp. 39–104.
- ⁷⁴V. Bucur, “Elastic constants of wood material,” in *Acoustics of Wood*, 2nd ed. (Springer, New York, 2006), Chap. 5, pp. 105–139.
- ⁷⁵V. Bucur, “Wood structural anisotropy and ultrasonic parameters,” in *Acoustics of Wood*, 2nd ed. (Springer, New York, 2006), Chap. 6, pp. 141–169.
- ⁷⁶H. Maurer, S. I. Schubert, F. Bächle, S. Clauss, D. Gsell, J. Dual, and P. Niemz, “A simple anisotropy correction procedure for acoustic wood tomography,” *Holzforschung* **60**(5), 567–573 (2006).
- ⁷⁷A. Dikrallah, B. Kabouchi, A. Hakam, L. Brancherieu, H. Bailleres, A. Famiri, and M. Ziani, “Study of acoustic wave propagation through the cross section of green wood,” *Compt. Rend. Méc.* **338**(2), 107–112 (2010).
- ⁷⁸G. Li, X. Wang, H. Feng, J. Wiedenbeck, and R. J. Ross, “Analysis of wave velocity patterns in black cherry trees and its effect on internal decay detection,” *Comput. Electron. Agric.* **104**, 32–39 (2014).
- ⁷⁹J. P. Armstrong, D. W. Patterson, and J. E. Sneedenberger, “Comparison of three equations for predicting stress wave velocity as a function of grain angle,” *Wood Fiber Sci.* **23**(1), 32–43 (1991).
- ⁸⁰H. Sakai, A. Minamisawa, and K. Takagi, “Effect of moisture content on ultrasonic velocity and attenuation in woods,” *Ultrasonics* **28**(6), 382–385 (1990).
- ⁸¹N. Sobue, “Simulation study on stress wave velocity in wood above fiber saturation point,” *Mokuzai Gakkaishi* **39**(3), 271–276 (1993).
- ⁸²J. Sandoz, “Moisture content and temperature effect on ultrasound timber grading,” *Wood Sci. Technol.* **27**, 373–380 (1993).
- ⁸³S.-Y. Wang, C.-M. Chiu, and C.-J. Lin, “Variations in ultrasonic wave velocity and dynamic Young’s modulus with moisture content for *Taiwania* plantation lumber,” *Wood Fiber Sci.* **34**(3), 370–381 (2002).
- ⁸⁴S.-Y. S.-Y. Wang, C.-J. Lin, and C.-M. Chiu, “The adjusted dynamic modulus of elasticity above the fiber saturation point in *Taiwania* plantation wood by ultrasonic-wave measurement,” *Holzforschung* **57**(5), 547–552 (2003).
- ⁸⁵F. G. R. d. Oliveira, M. Candian, F. F. Lucchette, J. L. Salgon, and A. Sales, “Moisture content effect on ultrasonic velocity in *Goumia glabra*,” *Mater. Res.* **8**(1), 11–14 (2005).
- ⁸⁶J. Moreno Chan, “Moisture content in radiata pine wood: Implications for wood quality and water-stress response,” Ph.D. thesis, School of Forestry, University of Canterbury, Christchurch, New Zealand, 2007, 203 pp.
- ⁸⁷X. Wang, “Effects of size and moisture on stress wave E-rating of structural lumber,” in *Proceedings of the 10th World Conference on Timber Engineering* (Miyazaki, Japan, 2008).
- ⁸⁸S. Gao, W. Xiping, L. Wang, and R. B. Allison, “Modeling temperature and moisture state effects on acoustic velocity in wood,” in *Proceedings of the 17th International Symposium on Nondestructive Testing And Evaluation of Wood*, Sopron, Hungary (2011), pp. 411–418.
- ⁸⁹H. Unterwieser and G. Schickhofer, “Influence of moisture content of wood on sound velocity and dynamic MOE of natural frequency- and ultrasonic runtime measurement,” *Eur. J. Wood Wood Products* **69**(2), 171–181 (2011).
- ⁹⁰C. Senalik, “Detection and assessment of wood decay-glulam beams and wooden utility poles,” Ph.D. thesis, University of Illinois at Urbana-Champaign, Champaign, IL, 2013, 232 pp.
- ⁹¹H. Bächle and J. Walker, “The influence of temperature on the velocity of sound in green pine wood,” *Eur. J. Wood Wood Products* **64**(5), 429–430 (2006).
- ⁹²H. D. Xu, “Research on stress wave propagation velocity in both frozen and unfrozen wood,” Ph.D. thesis, Northeast Forestry University, Heilongjiang, China, 2012.
- ⁹³S. Gao, X. Wang, L. Wang, and R. B. Allison, “Effect of temperature on acoustic evaluation of standing trees and logs: Part 1: Laboratory investigation,” *Wood Fiber Sci.* **44**(3), 286–297 (2012).
- ⁹⁴S. Gao, X. Wang, L. Wang, and R. B. Allison, “Effect of temperature on acoustic evaluation of standing trees and logs: Part 2: Field investigation,” *Wood Fiber Sci.* **45**(1), 15–25 (2013).
- ⁹⁵H. Xu and L. Wang, “A preliminary explanation for subzero temperature effect on stress wave velocity in green Korean pine wood,” in *2012 International Conference on Biobase Material Science and Engineering (BMSE)* (IEEE, New York, 2012), pp. 271–275.
- ⁹⁶H. Xu and L. Wang, “Analysis of cold temperature effect on stress wave velocity in green wood,” *Holzforschung* **68**(6), 693–698 (2014).
- ⁹⁷W. Lihai, G. Shan, W. Yang, and X. Huadong, “Transmitting velocity of stress wave in birch standing trees in frozen state,” *J. Northeast For. Univ.* **36**, 36–38 (2008).
- ⁹⁸S. Gao, L. Wang, and Y. Wang, “A comparative study on the velocities of stress wave propagation in standing *Fraxinus mandshurica* trees in frozen and non-frozen states,” *Front. For. China* **4**, 382–387 (2009).

- ⁹⁹G. Shan, W. Lihai, and W. Yang, "Experimental study on stress wave propagation velocity in frozen standing trees of 10 species in Northeast China," *For. Eng.* **4**, 47–52 (2013).
- ¹⁰⁰C. Guillaume, C.-V. Katline, L. Benoit, A. Thierry, and M. Stefan, "Changes in ultrasound velocity and attenuation indicate freezing of xylem sap," *Agric. For. Meteorol.* **185**, 20–25 (2014).
- ¹⁰¹M. Andrews, "Which acoustic speed," in *Proceedings of the 13th International Symposium on Nondestructive Testing of Wood* (2002), Vol. 2003, pp. 159–165.
- ¹⁰²X. Wang, R. J. Ross, and P. Carter, "Acoustic evaluation of wood quality in standing trees. Part. I. Acoustic wave behavior," *Wood Fiber Sci.* **39**(1), 28–38 (2007).
- ¹⁰³H. Zhang, X. Wang, and R. J. Ross, "Stress wave propagation on standing trees: Part 1. Time-of-flight measurement and 2D stress wave contour maps," in *16th International Symposium on NDT/NDE of Wood* (Beijing Forestry University, Beijing, China, 2009), pp. 12–14.
- ¹⁰⁴J. Su, H. Zhang, and X. Wang, "Stress wave propagation on standing trees-Part 2. formation of 3D stress wave contour maps," in *Series: Conference Proceedings* (2009), pp. 59–64.
- ¹⁰⁵H. Zhang, X. Wang, and J. Su, "Experimental investigation of stress wave propagation in standing trees," *Holzforschung* **65**(5), 743–748 (2011).
- ¹⁰⁶G. Searles, "Acoustic segregation and structural timber production," Ph.D. thesis, Edinburgh Napier University, Edinburgh, UK, 2012, 218 pp.
- ¹⁰⁷M. Andrews, "Where are we with sonics," in *Proceedings of the Wood Technology Research Centre Workshop 2000: Capturing the Benefits of Forestry Research* (University of Canterbury, Christchurch, New Zealand, 2000), pp. 57–61.
- ¹⁰⁸J. W. S. B. Rayleigh, *The Theory of Sound* (Macmillan, London, UK, 1896), Vol. 2.
- ¹⁰⁹M. J. Lowe, D. N. Alleyne, and P. Cawley, "Defect detection in pipes using guided waves," *Ultrasonics* **36**(1), 147–154 (1998).
- ¹¹⁰J. L. Rose, "A baseline and vision of ultrasonic guided wave inspection potential," *J. Pressure Vessel Technol.* **124**(3), 273–282 (2002).
- ¹¹¹J. L. Rose, *Ultrasonic Waves in Solid Media* (Cambridge University Press, Cambridge, UK, 2004), 454 pp.
- ¹¹²Z. Su, L. Ye, and Y. Lu, "Guided Lamb waves for identification of damage in composite structures: A review," *J. Sound Vib.* **295**(3), 753–780 (2006).
- ¹¹³I. A. Veres and M. B. Sayir, "Wave propagation in a wooden bar," *Ultrasonics* **42**(1), 495–499 (2004).
- ¹¹⁴S. Dahmen, H. Ketata, M. H. Ben Ghzlen, and B. Hosten, "Elastic constants measurement of anisotropic olivier wood plates using air-coupled transducers generated Lamb wave and ultrasonic bulk wave," *Ultrasonics* **50**(4), 502–507 (2010).
- ¹¹⁵P. Martin and J. Berger, "Waves in wood: Free vibrations of a wooden pole," *J. Mech. Phys. Solids* **49**(5), 1155–1178 (2001).
- ¹¹⁶P. Martin and J. Berger, "Waves in wood: Axisymmetric guided waves along boreholes," *Chin. J. Mech. Ser. A* **19**(1), 105–111 (2003).
- ¹¹⁷H. Yang, L. Wang, and L. Li, "Frequency equation of axisymmetric guided waves in logs," in *2011 International Conference on Electronic and Mechanical Engineering and Information Technology (EMEIT)* (IEEE, New York, 2011), Vol. 4, pp. 1964–1967.
- ¹¹⁸M. Subhani, J. Li, and B. Samali, "A comparative study of guided wave propagation in timber poles with isotropic and transversely isotropic material models," *J. Civ. Struct. Health Monit.* **3**(2), 65–79 (2013).
- ¹¹⁹G. Marra, R. Pellerin, and W. Galligan, "Nondestructive determination of wood strength and elasticity by vibration," *Holz Roh- Werkst.* **24**(10), 460–466 (1966).
- ¹²⁰A. Bartholomeu, R. Gonçalves, and V. Bucur, "Dispersion of ultrasonic waves in eucalyptus lumber as a function of the geometry of boards," *Sci. For.* **1**(63), 235–240 (2003).
- ¹²¹F. Divos, L. Denes, and G. Iniguez, "Effect of cross-sectional change of a board specimen on stress wave velocity determination," *Holzforschung* **59**(2), 230–231 (2005).
- ¹²²F. de Oliveira, K. Miller, M. Candian, and A. Sales, "Effect of the size of the specimen on ultrasonic velocity," *Rev. Arvore* **30**(1), 141–145 (2006).
- ¹²³A. Baltrušaitis, K. Ukalbergienė, V. Pranckevičienė, and L. Kaunas, "Nondestructive evaluation of viscous-elastic changes in ammonia-modified wood using ultrasonic and vibrant techniques," *Wood Res.* **55**(4), 39–50 (2010).
- ¹²⁴M. Grabianowski, B. Manley, and J. Walker, "Acoustic measurements on standing trees, logs and green lumber," *Wood Sci. Technol.* **40**(3), 205–216 (2006).
- ¹²⁵X. Wang, R. Ross, J. Erickson, J. Forsman, G. McGinnis, and R. de Groot, "Nondestructive methods of evaluating quality of wood in preservative-treated piles," Technical Report FPL-RN-0274, Madison, WI (2000), 9 pp.
- ¹²⁶C. Y. Hsu, "Radiata pine wood anatomy structure and biophysical properties," Ph.D. thesis, School of Forestry, University of Canterbury, Christchurch, New Zealand, 2003, 147 pp.
- ¹²⁷C.-M. Chiu, C.-H. Lin, and T.-H. Yang, "Application of nondestructive methods to evaluate mechanical properties of 32-year-old Taiwan incense cedar (*Calocedrus formosana*) wood," *BioResources* **8**(1), 688–700 (2012).
- ¹²⁸B. Dowding and G. Murphy, "Estimating within tree spatial changes in acoustic velocity in felled Douglas-fir stems," *Int. J. For. Eng.* **22**(1), 24–34 (2011).
- ¹²⁹X. Wang, S. Verrill, E. Lowell, R. J. Ross, and V. L. Herian, "Acoustic sorting models for improved log segregation," *Wood Fiber Sci.* **45**(4), 343–352 (2013).
- ¹³⁰M. J. Waghorn, E. G. Mason, and M. S. Watt, "Influence of initial stand density and genotype on longitudinal variation in modulus of elasticity for 17-year-old *Pinus radiata*," *For. Ecol. Manage.* **252**(1), 67–72 (2007).
- ¹³¹D. J. Cown and D. L. McConchie, "Wood property variations in an old-crop stand of radiata pine," *N. Z. J. For. Sci.* **10**(3), 508–520 (1980).
- ¹³²J. Chazelas, A. Vergne, and V. Bucur, "Analyse de la variation des propriétés physiques et mécaniques locales du bois autour des noeuds" ("Wood local properties variation around knots"), in *Actes du Colloque Comportement Mécanique du Bois*, Bordeaux, June 1988, pp. 376–386.
- ¹³³C. Gerhards, "Effect of knots on stress waves in lumber," Technical Report FPL-384, Forest Service, Forest Products Laboratory, US Department of Agriculture, Madison, WI (1982), 28 pp.
- ¹³⁴M. E. Schafer, "Ultrasound for defect detection and grading in wood and lumber," in *2000 IEEE Ultrasonics Symposium* (IEEE, New York, 2000), Vol. 1, pp. 771–778.
- ¹³⁵H. J. Hansen, "Acoustic studies on wood," Master's thesis, School of Forestry, University of Canterbury, Christchurch, New Zealand, 2006, 146 pp.
- ¹³⁶T. G. Jones and G. W. Emms, "Influence of acoustic velocity, density, and knots on the stiffness grade outturn of radiata pine logs," *Wood Fiber Sci.* **42**(1), 1–9 (2010).
- ¹³⁷J.-P. Lasserre, E. Mason, and M. Watt, "The influence of initial stocking on corewood stiffness in a clonal experiment of 11 year-old *Pinus radiata* D. Don," *N. Z. J. For.* **49**, 18–23 (2004).
- ¹³⁸X. Wang, R. J. Ross, B. K. Brashaw, J. Punches, J. R. Erickson, J. W. Forsman, and R. F. Pellerin, "Diameter effect on stress-wave evaluation of modulus of elasticity of logs," *Wood Fiber Sci.* **36**(3), 368–377 (2004).
- ¹³⁹G. Johnson and B. L. Gartner, "Genetic variation in basic density and modulus of elasticity of coastal Douglas-fir," *Tree Genet. Genomes* **3**(1), 25–33 (2006).
- ¹⁴⁰J.-P. Lasserre, E. G. Mason, and M. S. Watt, "Influence of the main and interactive effects of site, stand stocking and clone on *Pinus radiata* D. Don corewood modulus of elasticity," *For. Ecol. Manage.* **255**(8), 3455–3459 (2008).
- ¹⁴¹G. Searles and J. Moore, "Measurement of wood stiffness in standing trees and logs: Implications for end-product quality," *COST E53-Bled 21*, 1–5 (2009).
- ¹⁴²E. Lowell, C. L. Todoroki, D. P. Dykstra, and D. G. Briggs, "Linking acoustic velocity of standing Douglas-fir trees to veneer stiffness: A tree-log-product study across thinning treatments," *N. Z. J. For. Sci.* **44**(1), 1–16 (2014).
- ¹⁴³B. E. Roth, X. Li, D. A. Huber, and G. F. Peter, "Effects of management intensity, genetics and planting density on wood stiffness in a plantation of juvenile loblolly pine in the southeastern USA," *For. Ecol. Manage.* **246**(2), 155–162 (2007).
- ¹⁴⁴E. Warren, R. G. B. Smith, L. A. Apolaza, and J. C. Walker, "Effect of stocking on juvenile wood stiffness for three *Eucalyptus* species," *New For.* **37**(3), 241–250 (2009).
- ¹⁴⁵M. J. Waghorn and M. S. Watt, "Stand variation in *Pinus radiata* and its relationship with allometric scaling and critical buckling height," *Ann. Botany* **111**(4), 675–680 (2013).
- ¹⁴⁶D. Auty and A. Achim, "The relationship between standing tree acoustic assessment and timber quality in Scots pine and the practical implications

- for assessing timber quality from naturally regenerated stands," *Forestry* **81**(6), 475–487 (2008).
- ¹⁴⁷R. Gonçalves, C. B. Pedroso, and M. V. Massak, "Acoustic and bending properties in *Pinus elliottii* beams obtained from trees of different ages," *J. Wood Sci.* **59**(2), 127–132 (2013).
- ¹⁴⁸L. Watson, "Evaluating the effects of initial stocking, physiological age and species on wood stiffness," Bachelor thesis, School of Forestry, University of Canterbury, Christchurch, New Zealand, 2013, 42 pp.
- ¹⁴⁹J.-M. Leban and D. W. Haines, "The modulus of elasticity of hybrid larch predicted by density, rings per centimeter, and age," *Wood Fiber Sci.* **31**(4), 394–402 (1999).
- ¹⁵⁰B. Jayne, "Vibrational properties of wood as indices of quality," *For. Prod. J.* **9**(11), 413–416 (1959).
- ¹⁵¹R. Hearmon, "The influence of shear and rotatory inertia on the free flexural vibration of wooden beams," *Br. J. Appl. Phys.* **9**(10), 381–389 (1958).
- ¹⁵²R. F. Pellerin, "A vibrational approach to nondestructive testing of structural lumber," *For. Prod. J.* **15**(3), 93–101 (1965).
- ¹⁵³N. Sobue, "Instantaneous measurement of elastic constants by analysis of the tap tone of wood: Application to flexural vibration of beams," *Mokuzai Gakkaishi* **32**(4), 274–279 (1986).
- ¹⁵⁴Y. Fujisawa, S. Ohta, K. Nishimura, and M. Tajima, "Wood characteristics and genetic variations in sugi (*Cryptomeria japonica*): Clonal differences and correlations between locations of dynamic moduli of elasticity and diameter growths in plus-tree clones," *Mokuzai Gakkaishi* **38**(7), 638–644 (1992).
- ¹⁵⁵S. Aratake and T. Arima, "Estimation of modulus of rupture (MOR) and modulus of elasticity (MOE) of lumber using higher natural frequency of log in-pile: 2. Possibility of application for sugi square lumber with pith," *Mokuzai Gakkaishi* **40**(9), 1003–1007 (1994).
- ¹⁵⁶S. Aratake, T. Arima, T. Sakoda, and Y. Nakamura, "Estimation of modulus of rupture (MOR) and modulus of elasticity (MOE) of lumber using higher natural frequency of log in pile of logs: Possibility of application for sugi scaffolding board," *Mokuzai Gakkaishi* **38**(11), 995–1001 (1992).
- ¹⁵⁷T. Arima, N. Nakamura, S. Maruyama, and S. Hayamura, "Natural frequency of log and lumber hit with hammer and applications for production processing," in *Proceedings of the International Timber Engineering Conference*, 23–25 October 1990, pp. 527–533.
- ¹⁵⁸T. Arima, "Kokusan zai tokuni sugi zai no ryo kaihatsu sisutemu tositenou toukyu kubun" ("Grading as a system for the development of Japanese wood utilisation, especially sugi wood"), in *Trial for Measuring Wood Properties of Standing Tree by Vibrational Method and Development of New Method for Thinning According to the Wood Properties of Standing Tree*, edited by M. Ohkuma (Tokyo University, Tokyo, Japan, 1991), pp. 69–78.
- ¹⁵⁹P. Harris, R. Petherick, and M. Andrews, "Acoustic resonance tools," in *Proceedings of the 13th International Symposium on Nondestructive Testing of Wood* (2002), pp. 195–201.
- ¹⁶⁰H. Lindstrom, P. Harris, and R. Nakada, "Methods for measuring stiffness of young trees," *Holz Roh- Werkst.* **60**(3), 165–174 (2002).
- ¹⁶¹W. D. Snyder, E. Christensen, S. L. Floyd, L. H. Jones, C. K. Kendall, B. B. Pearce, E. Shaw, and M. J. Yancey, "Log cutting optimization system," U.S. patent 6,026,689 (February 22, 2000).
- ¹⁶²D. Amishev and G. E. Murphy, "Implementing resonance-based acoustic technology on mechanical harvesters/processors for real-time wood stiffness assessment: Opportunities and considerations," *Int. J. For. Eng.* **19**(2), 48–56 (2008).
- ¹⁶³D. Y. Amishev, "In-forest log segregation based on acoustic measurement of wood stiffness," Ph.D. thesis, Department of Forest Engineering, Oregon State University, Corvallis, OR, 2008, 272 pp.
- ¹⁶⁴See www.fibre-gen.com.
- ¹⁶⁵Fibre-gen, "HITMAN HM200: Log segregation for value recovery: Brochure," http://media.wix.com/ugd/e02948_1307fa5b3ee64a8ba97f09fce0848cc8.pdf (Last viewed January 2016).
- ¹⁶⁶P. Carter, S. Chauhan, and J. Walker, "Sorting logs and lumber for stiffness using director HM200," *Wood Fiber Sci.* **38**(1), 49–54 (2006).
- ¹⁶⁷A. Achim, N. Paradis, P. Carter, and R. E. Hernández, "Using acoustic sensors to improve the efficiency of the forest value chain in Canada: A case study with laminated veneer lumber," *Sensors* **11**(6), 5716–5728 (2011).
- ¹⁶⁸See <http://www.fakopp.com>.
- ¹⁶⁹Fakopp Enterprise Bt and G. Divos, "Resonance log garder: POCKETPC software: User guide," http://www.fakopp.com/site/downloads/RLG_Guide.pdf (Last viewed April 2014).
- ¹⁷⁰Fibre-gen, "HITMAN LG640: Automated log segregation for value recovery: Brochure," <http://www.fibre-gen.com/pdf/LG640Brochure.pdf> (Last viewed August 2014).
- ¹⁷¹J. Parker and G. Searles, "Density segregation through acoustics and microwave technologies: New tools being developed and adopted by CHH sawmills. Practical tools and new technologies to improve segregation of logs and lumber for processing," in *Proceedings of Wood Quality 2004* (Albury, NSW, Australia, 2004).
- ¹⁷²Metriguard Inc., "2350 sonic lumber grader: Brochure," <http://www.metriguard.com/catalog/2350V1.0.pdf> (Last viewed September 2014).
- ¹⁷³A. L. S. C. A. M. G. Lumber, "Grading machines approved by the board of review," http://www.alsc.org/greenbook%20collection/grading_machines.pdf (Last viewed December 2014).
- ¹⁷⁴S. S. Chauhan, K. M. Entwistle, and J. C. Walker, "Differences in acoustic velocity by resonance and transit-time methods in an anisotropic laminated wood medium," *Holzforschung* **59**(4), 428–434 (2005).
- ¹⁷⁵M. Andrews, "Wood quality measurement -son et lumière," *N. Z. J. For.* **47**, 19–21 (2002).
- ¹⁷⁶J.-P. Lasserre, E. G. Mason, and M. S. Watt, "Assessing corewood acoustic velocity and modulus of elasticity with two impact based instruments in 11-year-old trees from a clonal-spacing experiment of *Pinus radiata* D. Don," *For. Ecol. Manage.* **239**(1), 217–221 (2007).
- ¹⁷⁷G. W. Emms, B. Nanayakkara, and J. J. Harrington, "Application of longitudinal-wave time-of-flight sound speed measurement to *Pinus radiata* seedlings," *Can. J. For. Res.* **43**(8), 750–756 (2013).
- ¹⁷⁸E. R. d. S. Leite, P. R. G. Hein, T. M. d. Souza, and G. F. Rabelo, "Estimation of the dynamic elastic properties of wood from *Copaiifera langsdorffii* Desf using resonance analysis," *Cerne* **18**(1), 41–47 (2012).
- ¹⁷⁹D. Ouis, "Vibrational and acoustical experiments on logs of spruce," *Wood Sci. Technol.* **33**(2), 151–184 (1999).
- ¹⁸⁰D. Ouis, "Detection of decay in logs through measuring the dampening of bending vibrations by means of a room acoustical technique," *Wood Sci. Technol.* **34**(3), 221–236 (2000).
- ¹⁸¹D. Ouis, "Detection of rot in standing trees by means of an acoustic technique," *Arboricult. J.* **25**(2), 117–152 (2001).
- ¹⁸²J. Axmon, M. Hansson, and L. Sörnmo, "Experimental study on the possibility of detecting internal decay in standing *Picea abies* by blind impact response analysis," *Forestry* **77**(3), 179–192 (2004).
- ¹⁸³A. N. Mucciardi, C. J. Luley, and K. H. Gormally, "Preliminary evidence for using statistical classification of vibration waveforms as an initial decay detection tool," *Arboricult. Urban For.* **37**(5), 191–199 (2011).
- ¹⁸⁴F. Tallavo, M. D. Pandey, and G. Cascante, "Experimental and numerical methods for detection of voids in wood poles using ultrasonic testing," *J. Mater. Civ. Eng.* **25**(6), 772–780 (2013).
- ¹⁸⁵X. Wang, R. J. Ross, M. McClellan, R. J. Barbour, J. R. Erickson, J. W. Forsman, and G. D. McGinnis, "Strength and stiffness assessment of standing trees using a nondestructive stress wave technique," Research Paper FPL-RP-585, Forest Products Laboratory, US Department of Agriculture, Madison, WI (2000), 9 pp.
- ¹⁸⁶X. Wang, R. J. Ross, M. McClellan, R. J. Barbour, J. R. Erickson, J. W. Forsman, and G. D. McGinnis, "Nondestructive evaluation of standing trees with a stress wave method," *Wood Fiber Sci.* **33**(4), 522–533 (2001).
- ¹⁸⁷C.-L. Huang, "System and method for measuring stiffness in standing trees," U.S. patent 6,871,545 (March 29, 2005).
- ¹⁸⁸X. Wang, N. Sharplin, P. Carter, and R. J. Ross, "Method and apparatus for evaluation of standing timber," U.S. patent 7,418,866 (September 2, 2008).
- ¹⁸⁹M. J. Toulmin and C. Raymond, "Developing a sampling strategy for measuring acoustic velocity in standing *Pinus radiata* using the TreeTap time of flight tool," *N. Z. J. For. Sci.* **37**(1), 96–111 (2007).
- ¹⁹⁰S. N. Woods, "Acoustic inspection of timber," Master's thesis, Electrical and Computer Engineering, University of Canterbury, Christchurch, New Zealand, 2006, 101 pp.
- ¹⁹¹D. Walsh, M. Strandgard, and P. Carter, "Evaluation of the Hitman PH330 acoustic assessment system for harvesters," *Scand. J. For. Res.* **29**(6), 593–602 (2014).
- ¹⁹²J. Sandoz, Y. Benoit, and L. Demay, "Wood testing using acousto-ultrasonic," in *12th International Symposium on Nondestructive Testing of Wood* (2000), pp. 97–104.
- ¹⁹³J.-L. Sandoz and Y. Benoit, "Timber grading machine using ultrasonic and density measurements: Triomatic," in *15th International Symposium on Nondestructive Testing of Wood* (Duluth, MN, 2007), pp. 10–12.

- ¹⁹⁴M. Hayes and J. Chen, "A portable stress wave measurement system for timber inspection," in *Proceedings of the Electronics Conference (ENZCON)* (Hamilton, New Zealand, 2003), pp. 1–6.
- ¹⁹⁵A. C. Matheson, R. L. Dickson, D. J. Spencer, B. Joe, and J. Ilic, "Acoustic segregation of *Pinus radiata* logs according to stiffness," *Ann. For. Sci.* **59**(5), 471–477 (2002).
- ¹⁹⁶R. L. Dickson, C. A. Raymond, W. Joe, and C. A. Wilkinson, "Segregation of *Eucalyptus dunnii* logs using acoustics," *For. Ecol. Manage.* **179**(1), 243–251 (2003).
- ¹⁹⁷R. Dickson, A. Matheson, B. Joe, J. Ilic, and J. Owen, "Acoustic segregation of *Pinus radiata* logs for sawmilling," *N. Z. J. For. Sci.* **34**(2), 175–189 (2004).
- ¹⁹⁸B. Joe, R. Dickson, C. Raymond, J. Ilic, and A. Matheson, "Prediction of *Eucalyptus dunnii* and *Pinus radiata* timber stiffness using acoustics, final report," Technical Report 04/013, Project No. PN99.2010, Rural Industries Research and Development Corporation, Australian Capital Territory (2004), 118 pp.
- ¹⁹⁹J. M. Mahon, "The use of acoustics for the wood quality assessment of standing *P. taeda* trees," Ph.D. thesis, University of Georgia Athens, GA, 2007, 63 pp.
- ²⁰⁰J. M. Mahon, L. Jordan, L. R. Schimleck, A. Clark, and R. F. Daniels, "A comparison of sampling methods for a standing tree acoustic device," *Southern J. Appl. For.* **33**(2), 62–68 (2009).
- ²⁰¹R. J. Ross, K. A. McDonald, D. W. Green, and K. C. Schad, "Relationship between log and lumber modulus of elasticity," *For. Prod. J.* **47**(2), 89–92 (1997).
- ²⁰²R. Booker, "Stiffness testing of standing trees," in *Proceedings 2nd New Zealand Wood Quality Workshop*. New Zealand Forest Research Institute Ltd, *FRI Bulletin*, edited by B. Ridout (Forest Research Institute, New Zealand Forest Service, Rotorua, New Zealand, 1997), Vol. 202, pp. 5–6.
- ²⁰³A. Tsehay, A. Buchanan, and J. Walker, "Log segregation into stiffness classes," in *2nd New Zealand Wood quality Workshop*, FRI Bulletin No. 202 (Forest Research Institute, New Zealand Forest Service, Rotorua, New Zealand, 1997), pp. 7–10.
- ²⁰⁴A. Buchanan, R. Nakada, and J. Walker, "Log segregation by stiffness class," in *3rd Wood Quality Symposium: Emerging Technologies for Wood Processing* (FIEA, Rotorua, New Zealand) (1999), 8 pp.
- ²⁰⁵B. G. Ridout, K. R. Wealleans, R. E. Booker, D. L. McConchie, and R. D. Ball, "Comparison of log segregation methods for structural lumber yield improvement," *For. Prod. J.* **49**(11), 63–66 (1999).
- ²⁰⁶S. S. Jang, "Evaluation of lumber properties by applying stress waves to larch logs grown in Korea," *For. Prod. J.* **50**(3), 44–48 (2000).
- ²⁰⁷A. Tsehay, A. Buchanan, and J. Walker, "Sorting of logs using acoustics," *Wood Sci. Technol.* **34**(4), 337–344 (2000).
- ²⁰⁸X. Wang, R. J. Ross, J. A. Mattson, J. R. Erickson, J. W. Forsman, E. A. Geske, and M. A. Wehr, "Nondestructive evaluation techniques for assessing modulus of elasticity and stiffness of small-diameter logs," *For. Prod. J.* **52**(2), 79–85 (2002).
- ²⁰⁹R. L. Dickson, B. Joe, P. Harris, S. Holtorf, and C. Wilkinson, "Acoustic segregation of Australian-grown *Pinus radiata* logs for structural board production," *Aust. For.* **67**(4), 261–266 (2004).
- ²¹⁰D. J. Albert, J. C. F. Walker, R. L. Dickson, and T. A. Clark, "Method of selecting and/or processing wood according to fibre characteristics," U.S. patent 6,773,552 (August 10, 2004).
- ²¹¹J. L. Sandoz, "Form and treatment effects on conical roundwood tested in bending," *Wood Sci. Technol.* **25**(3), 203–214 (1991).
- ²¹²F. Divos, "Acoustic tools for seedling, tree and log selection," in *The Future of Quality Control for Wood and Wood Products* (Edinburgh, UK, 2010), pp. 5–9, available at <http://www.coste53.net/downloads/Edinburgh/Edinburgh-Presentation/51.pdf>.
- ²¹³G. Emms, B. Nanayakkara, and J. Harrington, "A novel technique for non-damaging measurement of sound speed in seedlings," *Eur. J. For. Res.* **131**(5), 1449–1459 (2012).
- ²¹⁴Fibre-gen, "HITMAN PH330: Automated wood quality measurement for log making and segregation: Brochure," http://media.wix.com/ugd/e02948_50a4bf861b0e40968b1872d333f6fd9e.pdf (Last viewed January 2016).
- ²¹⁵Fakopp Enterprise Bt, "TreeSonic microsecond timer users guide," http://www.fakopp.com/site/downloads/TreeSonic_Guide.pdf (Last viewed April 2014).
- ²¹⁶C. G. Mattheck and K. A. Bethge, "Detection of decay in trees with Metriguard stress wave timer," *J. Arboricul.* **19**, 374–374 (1993).
- ²¹⁷Metriguard Inc., "Field and laboratory equipment: Brochure," <http://www.metrigraph.com/catalog/47%20-%2056%20Field%20&%20Lab%20Equipment.pdf> (Last viewed September 2014).
- ²¹⁸See http://www.imlusa.com/html/ml_micro_hammer.html.
- ²¹⁹Fakopp Enterprise Bt, "Fakopp ultrasonic timer: User's guide," http://www.fakopp.com/site/downloads/Ultrasonic_Timer.pdf (Last viewed March 2015).
- ²²⁰See www.agricef.com.br.
- ²²¹CBS-CBT Technologies, "Sylvatest Trio," <http://www.cbs-cbt.com/fr/technologie/technologie-sylvatest-5-112-5> (Last viewed January 2016).
- ²²²See www.geinspectiontechnologies.com.
- ²²³J.-L. Sandoz and B. Yann, "Timber grading machine using multivariate parameters based on ultrasonic and density measurement," in *COST E 53 Conference—Quality Control for Wood and Wood Products* (Warsaw, Poland, 2007), pp. 167–173, available at <http://www.coste53.net/downloads/Warsaw/Warsaw-presentation/COSTE53-ConferenceWarsaw-Presentation-Sandoz.pdf>.
- ²²⁴CBS-CBT Group, "Trimatic: Flyer," http://www.cbs-cbt.com/New_site/FR/Downloads/Triomatic/triomatic_flyer2009.pdf (Last viewed September 2014).
- ²²⁵Metriguard Inc., "Veneer testers: Brochure," <http://www.metrigraph.com/catalog/5%20-%202016%20Veneer%20Testers.pdf> (Last viewed September 2014).
- ²²⁶Metriguard Inc., "Green end veneer grading now possible with the metriguard 2815 mtp green veneer tester: Brochure," <http://www.metrigraph.com/catalog/Pub%201027%20-%20202815%20MTP%20Green%20Veneer%20Tester.pdf> (Last viewed September 2014).
- ²²⁷B. M. Wing, "Variation in standing tree acoustic velocity measurements using the Director ST300 time of flight tool," in *Proceedings of the First Annual Forest Engineering, Resources, and Management Department Graduate Symposium*, Oregon State University, June 4, 2009, pp. 67–74.
- ²²⁸C. R. Mora, L. R. Schimleck, F. Isik, J. M. Mahon, A. Clark, and R. F. Daniels, "Relationships between acoustic variables and different measures of stiffness in standing *Pinus taeda* trees," *Can. J. For. Res.* **39**(8), 1421–1429 (2009).
- ²²⁹Z. Hong, A. Fries, S.-O. Lundqvist, B. Andersson Gull, and H. X. Wu, "Measuring stiffness using acoustic tool for Scots pine breeding selection," *Scand. J. For. Res.* **30**(4), 363–372 (2015).
- ²³⁰N. Paradis, D. Auty, P. Carter, and A. Achim, "Using a standing-tree acoustic tool to identify forest stands for the production of mechanically-graded lumber," *Sensors* **13**(3), 3394–3408 (2013).
- ²³¹R. J. Ross and X. Wang, "A review of the use of acoustic speed to assess standing timber quality," https://www.researchgate.net/publication/267862770_A_Review_of_the_Use_of_Acoustic_Speed_to_Assess_Standing_Timber_Quality_Basic_Science (Last viewed January 2016).
- ²³²Y. Yin, H. Nagao, X. Liu, and T. Nakai, "Mechanical properties assessment of *Cunninghamia lanceolata* plantation wood with three acoustic-based nondestructive methods," *J. Wood Sci.* **56**(1), 33–40 (2010).
- ²³³R. Gonçalves, C. B. Pedroso, M. V. Massak, F. Batista, and C. B. Secco, "Technical note: Velocity of ultrasonic waves in live trees and in freshly-felled logs," *Wood Fiber Sci.* **43**(2), 232–235 (2011).
- ²³⁴X. Wang, R. J. Ross, and P. Carter, "Acoustic evaluation of standing trees: Recent research development," in *Proceedings of the 14th International Symposium on Nondestructive Testing of Wood* (Shaker Verlag, Aachen, Germany, 2005), pp. 455–465.
- ²³⁵D. W. Haines, J.-M. Leban, and C. Herbé, "Determination of Young's modulus for spruce, fir and isotropic materials by the resonance flexure method with comparisons to static flexure and other dynamic methods," *Wood Sci. Technol.* **30**(4), 253–263 (1996).
- ²³⁶D. Ouis, "On the frequency dependence of the modulus of elasticity of wood," *Wood Sci. Technol.* **36**(4), 335–346 (2002).
- ²³⁷J.-L. Yang, J. Ilic, and T. Wardlaw, "Relationships between static and dynamic modulus of elasticity for a mixture of clear and decayed eucalypt wood," *Aust. For.* **66**(3), 193–196 (2003).
- ²³⁸J. Baar, J. Tippner, and V. Gryc, "The influence of wood density on longitudinal wave velocity determined by the ultrasound method in comparison to the resonance longitudinal method," *Eur. J. Wood Wood Products* **70**(5), 767–769 (2012).
- ²³⁹K. T. Hassan, P. Horáček, and J. Tippner, "Evaluation of stiffness and strength of Scots pine wood using resonance frequency and ultrasonic techniques," *BioResources* **8**(2), 1634–1645 (2013).
- ²⁴⁰D. Jacques, M. Marchal, and Y. Curnel, "Relative efficiency of alternative methods to evaluate wood stiffness in the frame of hybrid larch

- (*Larix × eurolepis* Henry) clonal selection," *Ann. For. Sci.* **61**(1), 35–43 (2004).
- ²⁴¹G. Alfredsen, E. Larnoy, and H. Militz, "Dynamic MOE testing of wood: The influence of wood protecting agents and moisture content on ultrasonic pulse and resonant vibration," *Wood Res. Slovak.* **51**(1), 11–20 (2006).
- ²⁴²J.-H. Jiang, J.-X. Lu, H.-Q. Ren, C. Long, and X.-Q. Luo, "Assessment of flexural properties of different grade dimension lumber by ultrasonic technique," *J. For. Res.* **18**(4), 305–308 (2007).
- ²⁴³M. Puaad, Z. Ahmad, and H. M. Azlan, "Ultrasonic wave non-destructive method for predicting the modulus of elasticity of timber," in *International Civil and Infrastructure Engineering Conference* (Springer, New York, 2013), pp. 85–96.
- ²⁴⁴X. Wang, "Fundamentals of acoustic measurements on trees and logs and their implication to field application," in *Proceedings 17th International Nondestructive Testing and Evaluation of Wood Symposium* (2011), pp. 25–33.
- ²⁴⁵A. Øvrum, "In-forest assessment of timber stiffness in Norway spruce (*Picea abies* (L.) Karst.)," *Eur. J. Wood Wood Products* **71**(4), 429–435 (2013).
- ²⁴⁶J. Edlund, "Methods for automatic grading of saw logs," Ph.D. thesis, Acta Universitatis Agriculturae Sueciae, Swedish University of Agricultural Sciences, Uppsala, 2004, 38 pp.
- ²⁴⁷J.-P. Lasserre, E. G. Mason, and M. S. Watt, "The effects of genotype and spacing on *Pinus radiata* [D. Don] corewood stiffness in an 11-year old experiment," *For. Ecol. Manage.* **205**(1), 375–383 (2005).
- ²⁴⁸S. D. Carson, D. J. Cown, R. B. McKinley, and J. R. Moore, "Effects of site, silviculture and seedlot on wood density and estimated wood stiffness in radiata pine at mid-rotation," *N. Z. J. For. Sci.* **44**(1), 1–12 (2014).
- ²⁴⁹S.-T. Chuang and S.-Y. Wang, "Evaluation of standing tree quality of Japanese cedar grown with different spacing using stress-wave and ultrasonic-wave methods," *J. Wood Sci.* **47**(4), 245–253 (2001).
- ²⁵⁰L. Soto, L. Valenzuela, and J. Lasserre, "Effect of initial planting density in dynamic modulus of elasticity in standing trees and logs of 28 years old radiata pine plantation in sandy soil, Chile," *Maderas Cien. Technol.* **14**(2), 209–224 (2012).
- ²⁵¹S. Wang, F. Lin, M. Jane, C. Lin, and C. Hung, "Effects of thinning and pruning on DBH and ultrasonic wave velocity in *Taiwania cryptomerioide*," in *World Conference on Timber Engineering* (Whistler Resort, Whistler, British Columbia, Canada, 2000), pp. 1–7.
- ²⁵²S.-Y. Wang, C.-J. Lin, C.-M. Chiu, J.-H. Chen, and T.-H. Yung, "Dynamic modulus of elasticity and bending properties of young *Taiwania* trees grown with different thinning and pruning treatments," *J. Wood Sci.* **51**(1), 1–6 (2005).
- ²⁵³J. Moore, A. J. Lyon, D. Ridley-Ellis, and B. A. Gardiner, "Properties of UK-grown Sitka spruce: Extent and sources of variation," in *Proceedings of the 10th World Conference on Timber Engineering, Miyazaki 2008* (Engineered Wood Products Association, Tacoma, WA, 2008), pp. 1–8.
- ²⁵⁴G. M. Downes, J. G. Nyakuengama, R. Evans, R. Northway, P. Blakemore, R. L. Dickson, and M. Lausberg, "Relationship between wood density, microfibril angle and stiffness in thinned and fertilized *Pinus radiata*," *IAWA J.* **23**(3), 253–266 (2002).
- ²⁵⁵D. J. Palmer, M. O. Kimberley, D. J. Cown, and R. B. McKinley, "Assessing prediction accuracy in a regression kriging surface of *Pinus radiata* outerwood density across New Zealand," *For. Ecol. Manage.* **308**, 9–16 (2013).
- ²⁵⁶X. Li, D. A. Huber, G. L. Powell, T. L. White, and G. F. Peter, "Breeding for improved growth and juvenile corewood stiffness in slash pine," *Can. J. For. Res.* **37**(10), 1886–1893 (2007).
- ²⁵⁷L. A. Apiolaza, J. C. Walker, H. Nair, and B. Butterfield, "Very early screening of wood quality for radiata pine: Pushing the envelope," in *Proceedings of the 51st International Convention of Society of Wood Science and Technology* (School of Biological Sciences, University of Canterbury, Christchurch, New Zealand, 2008), pp. 1–7.
- ²⁵⁸L. A. Apiolaza, "Very early selection for solid wood quality: Screening for early winners," *Ann. For. Sci.* **66**(6), 1–10 (2009).
- ²⁵⁹M. Ivković, W. J. Gapare, A. Abarquez, J. Illic, M. B. Powell, and H. X. Wu, "Prediction of wood stiffness, strength, and shrinkage in juvenile wood of radiata pine," *Wood Sci. Technol.* **43**(3), 237–257 (2009).
- ²⁶⁰L. A. Apiolaza, B. Butterfield, S. S. Chauhan, and J. C. Walker, "Characterization of mechanically perturbed young stems: Can it be used for wood quality screening?," *Ann. For. Sci.* **68**(2), 407–414 (2011).
- ²⁶¹L. A. Apiolaza, S. S. Chauhan, and J. C. Walker, "Genetic control of very early compression and opposite wood in *Pinus radiata* and its implications for selection," *Tree Genet. Genomes* **7**(3), 563–571 (2011).
- ²⁶²S. S. Chauhan and J. C. Walker, "Wood quality in artificially inclined 1-year-old trees of *Eucalyptus regnans* differences in tension wood and opposite wood properties," *Can. J. For. Res.* **41**(5), 930–937 (2011).
- ²⁶³L. A. Apiolaza, S. Chauhan, M. Hayes, R. Nakada, M. Sharma, and J. Walker, "Selection and breeding for wood quality a new approach," *N. Z. J. For.* **58**(1), 33–37 (2013).
- ²⁶⁴S. S. Chauhan, M. Sharma, J. Thomas, L. A. Apiolaza, D. A. Collings, and J. C. Walker, "Methods for the very early selection of *Pinus radiata* D. Don. for solid wood products," *Ann. For. Sci.* **70**(4), 439–449 (2013).
- ²⁶⁵B. Nanayakkara, M. Riddell, J. Harrington, and G. Emms, "Understanding the clonal response to imposed mechanical stress in *Pinus radiata* seedlings," in *Wood The Best Material for Mankind*, edited by J. Kúdela and M. Baabiak (Arbora Publishers, Zvolen, Slovakia, 2013), pp. 39–41.
- ²⁶⁶M. Sharma, "New approaches to wood quality assessment," Ph.D. thesis, School of Forestry, University of Canterbury, Christchurch, New Zealand, 2013, 172 pp.
- ²⁶⁷B. Nanayakkara, F. Lagane, P. Hodgkiss, M. Dibley, S. Smaill, M. Riddell, J. Harrington, and D. Cown, "Effects of induced drought and tilting on biomass allocation, wood properties, compression wood formation and chemical composition of young *Pinus radiata* genotypes (clones)," *Holzforschung* **68**(4), 455–465 (2014).
- ²⁶⁸S. S. Chauhan and J. Walker, "Relationships between longitudinal growth strain and some wood properties in *Eucalyptus nitens*," *Aust. For.* **67**(4), 254–260 (2004).
- ²⁶⁹S. Kumar, "Genetic parameter estimates for wood stiffness, strength, internal checking, and resin bleeding for radiata pine," *Can. J. For. Res.* **34**(12), 2601–2610 (2004).
- ²⁷⁰H. Lindstrom, R. Evans, and M. Reale, "Implications of selecting tree clones with high modulus of elasticity," *N. Z. J. For. Sci.* **35**(1), 50–71 (2005).
- ²⁷¹S. Kumar, H. Dungey, and A. Matheson, "Genetic parameters and strategies for genetic improvement of stiffness in radiata pine," *Silvae Genet.* **55**(2), 77–83 (2006).
- ²⁷²S. S. Chauhan, K. M. Entwistle, and J. C. Walker, "Search for a relationship between stress wave velocity and internal stresses in eucalypts and radiata pine," *Holzforschung* **61**(1), 60–64 (2007).
- ²⁷³S. Kumar and R. D. Burdon, "Genetic improvement of stiffness of radiata pine: Synthesis of results from acoustic assessments," *N. Z. J. For. Sci.* **40**, 185–197 (2010).
- ²⁷⁴S. S. Chauhan and P. Aggarwal, "Segregation of *Eucalyptus tereticornis* Sm. clones for properties relevant to solid wood products," *Ann. For. Sci.* **68**(3), 511–521 (2011).
- ²⁷⁵S. Chauhan and A. A. Kumar, "Assessment of variability in morphological and wood quality traits in *Melia dubia* Cav. for selection of superior trees," *J. Ind. Acad. Wood Sci.* **11**(1), 25–32 (2014).
- ²⁷⁶D. E. Kretschmann, "Mechanical properties of wood," *Environments* **5**, 34–79 (2012).